
**Petroleum, petrochemical and natural
gas industries — Composite repairs
for pipework — Qualification and
design, installation, testing and
inspection**

*Industries du pétrole, de la pétrochimie et du gaz naturel —
Réparations en matériau composite pour canalisations — Conformité
aux exigences de performance et conception, installation, essai et
inspection*

STANDARDSISO.COM : Click to view PDF of ISO 24817:2017



STANDARDSISO.COM : Click to view the full PDF of ISO 24817:2017



COPYRIGHT PROTECTED DOCUMENT

© ISO 2017, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents

Page

Foreword	v
Introduction	vi
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Symbols and abbreviated terms	6
4.1 Symbols	6
4.2 Abbreviated terms	9
5 Applications	9
6 Summary of key issues	11
7 Qualification and design	13
7.1 Repair feasibility assessment	13
7.2 Repair class	14
7.3 Repair design lifetime	14
7.4 Required data	15
7.4.1 Background	15
7.4.2 Original equipment design data	15
7.4.3 Maintenance and operational histories	15
7.4.4 Service condition data	15
7.4.5 Repair system qualification data	16
7.5 Design methodology	17
7.5.1 Overview	17
7.5.2 Environmental compatibility	19
7.5.3 Design temperature effects	19
7.5.4 Design based on substrate load sharing (defect type A)	21
7.5.5 Design based on repair laminate allowable strains (defect type A)	23
7.5.6 Design based on repair-allowable stresses determined by performance testing (defect type A)	24
7.5.7 Design of repairs for through-wall defects (defect type B)	25
7.5.8 Axial extent of repair	28
7.5.9 Optional design considerations	30
7.5.10 Dent and/or gouge type defects	34
7.5.11 Fretting type defects	34
7.5.12 Delamination or blister type defects	34
7.5.13 Repair of other components	35
7.5.14 Design output	38
7.6 Re-qualification of the repair system	38
7.6.1 Overview	38
7.6.2 For type A defect repairs	38
7.6.3 For type B defect repairs	38
8 Installation	39
8.1 Storage conditions	39
8.2 Documentation prior to repair application	39
8.2.1 Method statement	39
8.2.2 Work pack	39
8.3 Installer qualifications	40
8.4 Installation procedure	40
8.5 Repair completion documentation	41
8.6 Live repairs	43
8.7 Repair of clamps, piping components, tanks, or vessels	43
8.8 Environmental considerations	43

9	Testing and inspection	43
9.1	General	43
9.2	Allowable defects for the repair system	44
9.3	Repair of defects within the repair system	47
9.4	Inspection methods	48
9.5	Repair system maintenance and remedial options	48
9.5.1	Overview	48
9.5.2	Condition of the repair - visual inspection	48
9.5.3	Condition of the pipe substrate	49
9.5.4	Remedial options	49
9.5.5	Extension (revalidation) of repair design lifetime	49
9.5.6	Future modifications	50
10	System testing	50
11	Decommissioning	51
Annex A (normative)	Design data sheet	52
Annex B (normative)	Qualification data	55
Annex C (normative)	Short-term pipe spool survival test	59
Annex D (normative)	Measurement of γ_{LCL} for through-wall defect calculation	61
Annex E (normative)	Measurement of performance test data	64
Annex F (normative)	Measurement of impact performance	67
Annex G (normative)	Measurement of the degradation factor	68
Annex H (informative)	Axial extent of repair look-up table	70
Annex I (normative)	Installer qualification	72
Annex J (informative)	Installation requirements and guidance	75
Annex K (informative)	Design considerations	77
Annex L (informative)	Management of the integrity of composite repair systems to pipework and vessels	82
Bibliography		86

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 67, *Materials, equipment and offshore structures for petroleum, petrochemical and natural gas industries*, Subcommittee SC 6, *Processing equipment and systems*.

This second edition cancels and replaces the first edition (ISO 24817:2015), which has been technically revised.

This corrected version of ISO 24817:2017 incorporates the following correction:

- in 7.5.7, Formula (15), “D4” has been replaced by “D⁴”.

Introduction

The objective of this document is to ensure that pipework, pipelines, tanks and vessels repaired using composite systems that are qualified, designed, installed and inspected using this document will meet the specified performance requirements. Repair systems are designed for use within the petroleum, petrochemical and natural gas industries, and also within utility service applications. The main users of this document will be plant and equipment owners of the pipework and vessels, design contractors, suppliers contracted to provide the repair system, certifying authorities, installation, maintenance and inspection contractors.

STANDARDSISO.COM : Click to view the full PDF of ISO 24817:2017

Petroleum, petrochemical and natural gas industries — Composite repairs for pipework — Qualification and design, installation, testing and inspection

1 Scope

This document gives requirements and recommendations for the qualification and design, installation, testing and inspection for the external application of composite repair systems to corroded or damaged pipework, pipelines, tanks and vessels used in the petroleum, petrochemical and natural gas industries.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 75-3, *Plastics — Determination of temperature of deflection under load — Part 3: High-strength thermosetting laminates and long-fibre-reinforced plastics*

ISO 527-1, *Plastics — Determination of tensile properties — Part 1: General principles*

ISO 527-4, *Plastics — Determination of tensile properties — Part 4: Test conditions for isotropic and orthotropic fibre-reinforced plastic composites*

ISO 868, *Plastics and ebonite — Determination of indentation hardness by means of a durometer (Shore hardness)*

ISO 10952, *Plastics piping systems — Glass-reinforced thermosetting plastics (GRP) pipes and fittings — Determination of the resistance to chemical attack for the inside of a section in a deflected condition*

ISO 11357-2, *Plastics — Differential scanning calorimetry (DSC) — Part 2: Determination of glass transition temperature and glass transition step height*

ISO 11359-2, *Plastics — Thermomechanical analysis (TMA) — Part 2: Determination of coefficient of linear thermal expansion and glass transition temperature*

ISO 14692, *Petroleum and natural gas industries — Glass-reinforced plastics (GRP) piping*

ASTM C581, *Standard Practice for Determining Chemical Resistance of Thermosetting Resins Used in Glass-Reinforced Structures Intended for Liquid Service*

ASTM D543, *Standard Practices for Evaluating the Resistance of Plastics to Chemical Reagents*

ASTM D696, *Standard Test Method for Coefficient of Linear Thermal Expansion of Plastics Between Minus 30°C and 30°C with a Vitreous Silica Dilatometer*

ASTM D1598, *Standard Test Method for Time-to-Failure of Plastic Pipe under Constant Internal Pressure*

ASTM D1599, *Standard Test Method for Resistance to Short-Time Hydraulic Pressure of Plastic Pipe, Tubing, and Fittings*

ASTM D2583, *Standard Test Method for Indentation Hardness of Rigid Plastics by Means of a Barcol Impressor*

ASTM D2992, *Standard Practice for Obtaining Hydrostatic or Pressure Design Basis for Fiberglass (Glass-Fiber-Reinforced Thermosetting-Resin) Pipe and Fittings*

ASTM D3039, *Standard Test Method for Tensile Properties of Polymer Matrix Composite Materials*

ASTM D3165, *Standard Test Method for Strength Properties of Adhesives in Shear by Tension Loading of Single-Lap-Joint Laminated Assemblies*

ASTM D3681, *Standard Test Method for Chemical Resistance of Fiberglass (Glass-Fiber-Reinforced Thermosetting Resin) Pipe in a Deflected Condition*

ASTM D5379, *Standard Test Method for Shear Properties of Composite Materials by the V-Notched Beam Method*

ASTM D6604, *Standard Practice for Glass Transition Temperatures of Hydrocarbon Resins by Differential Scanning Calorimetry*

ASTM E831, *Standard Test Method for Linear Thermal Expansion of Solid Materials by Thermomechanical Analysis*

ASTM E1640, *Standard Test Method for Assignment of the Glass Transition Temperature by Dynamic Mechanical Analysis*

ASTM E2092, *Standard Test Method for Distortion Temperature in Three-Point Bending by Thermomechanical Analysis*

ASTM G8, *Standard Test Methods for Cathodic Disbonding of Pipeline Coatings*

BS 7910, *Guide to methods for assessing the acceptability of flaws in metallic structures*

EN 59, *Methods of testing plastics — Glass reinforced plastics — Measurement of hardness by means of a Barcol impressor (BS 2782-10, Method 1001, Measurement of hardness by means of a Barcol impressor)*

EN 1465, *Adhesives — Determination of tensile lap shear strength of rigid-to-rigid bonded assemblies*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <http://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1
anisotropic
exhibiting different physical properties in different directions

3.2
Barcol hardness
measure of surface hardness using a surface impresser

3.3
blister
air void between layers within the laminate visible on the surface as a raised area

3.4
composite
thermoset resin system that is reinforced by fibres

3.5
crack
split in the laminate extending through the wall (perpendicular to the surface) such that there is actual separation with opposite surfaces visible

3.6**cure
curing**

setting of a thermosetting resin system, such as polyester or epoxy, by an irreversible chemical reaction

3.7**cure schedule**

time-temperature profile qualified to generate a specified T_g or HDT

3.8**defect type A**

defect within the substrate, not through-wall and not expected to become through-wall within the repair design lifetime of the repair system

3.9**defect type B**

through-wall defect or a defect within the substrate where at the end of service life the remaining wall thickness is less than 1 mm

3.10**defined lifetime**

actual application or service lifetime of the repair

3.11**delamination**

area between the repair laminate and the substrate which should be bonded together but where no bond exists, or an area of separation between layers in the repair laminate

3.12**design lifetime**

maximum application lifetime of the repair

3.13**differential scanning calorimetry****DSC**

method of determining the glass transition temperature of a thermosetting resin

3.14**dry spot or un-impregnated/dry fibre**

area of fibre not impregnated with resin, with bare, exposed fibre visible

3.15**engineered repair**

repair which has been designed and applied under a specified, controlled process so that under the design conditions, there is a high degree of confidence that the repair will maintain its integrity over the design lifetime

3.16**exposed fibre**

area of fibre not impregnated with resin that projects from the body of the repair

3.17**foreign matter**

any substance other than the reinforcing fibre or other materials that form part of the repair system

3.18**finishing materials**

final layer of material to help compact the repair laminate, typically a polymeric film or a fabric

Note 1 to entry: They should be fully removed after the repair has hardened and before the repair is inspected or painted.

3.19

glass transition temperature

temperature at which a resin undergoes a marked change in physical properties

3.20

hardener

component added to a thermosetting resin to effect cure

3.21

heat distortion temperature

HDT

temperature at which a standard test bar deflects by a specified amount under a given load

3.22

installer

person who is qualified to apply a composite repair system

3.23

filler material

material used to repair external surface imperfections prior to the application of the composite laminate

3.24

laminate

repair laminate

part of a repair system that is the composite

Note 1 to entry: Most composites considered in this document are composed of discrete lamina or layers which are wrapped or stacked, one on top of the other. This stacked construction is the laminate.

3.25

layer

individual layer or wrap within the composite laminate

3.26

leak

condition of a substrate wall that can allow the contents to make contact with and act directly upon the (composite) repair laminate

Note 1 to entry: This does not refer to a fluid leaking through a hole or breach in the substrate.

3.27

occasional load

load that occurs rarely and during a short time

Note 1 to entry: Occasional loads typically occur less than 10 times in the life of the component and each load duration is less than 30 min.

3.28

owner

organization that owns or operates the substrate to be repaired

3.29

pin hole

pin-prick hole in the resin rich surface, not extending into the laminate

3.30

pipeline

pipe with components subject to the same design conditions used to transport fluids between plants

Note 1 to entry: Components include bends, flanges and valves.

3.31**pipework**

interconnected piping subject to the same set or sets of design conditions

3.32**piping****piping system**

assemblies of piping components used to convey fluids within a plant

Note 1 to entry: Components include pipe, fittings, flanges, gaskets, bolting and valves. A piping system is often above ground but sometimes buried.

3.33**pit**

depression in the surface of the laminate

3.34**ply**

single wrap or layer (lamina) of a repair laminate

3.35**post cure**

additional elevated-temperature cure applied after resin has hardened to ensure the required glass transition temperature is achieved

3.36**qualification application procedure**

application procedure used to apply the repair system for the qualification tests

3.37**qualification test temperature**

test temperature at which qualification testing of the repair system is performed

3.38**reinforcement**

fibre embedded in the resin system

Note 1 to entry: Possible fibre materials include aramid, carbon, glass, polyester, or similar materials. Reinforcement results in mechanical properties superior to those of the base resin.

3.39**repair system**

system comprised of the substrate, composite material (repair laminate), filler material, adhesive and including surface preparation and installation methods, used for repair of pipework

3.40**repair system installer**

company that installs the repair system

3.41**repair system supplier**

company that designs and supplies the repair system

3.42**resin system**

all of the components that make up the matrix portion of a composite

Note 1 to entry: Often this includes a resin, filler(s), pigment, mechanical property modifiers and catalyst or hardener.

3.43

risk

event encompassing what can happen (scenario), its likelihood (probability) and its level or degree of damage (consequences)

3.44

substrate

surface on which a repair is carried out

Note 1 to entry: The surface may belong to original pipework, pipework component, pipeline, tank, or vessel.

3.45

supervisor

experienced installer who is qualified by successfully completing the supervisor training course

3.46

Shore hardness

measure of surface hardness using a surface impresser or durometer

3.47

thermoset resin system

resin system that cannot be melted or remoulded following polymerization

3.48

wrinkle

wavy surface or distinct ridge in the laminate where the reinforcing fabric has creased during application

4 Symbols and abbreviated terms

4.1 Symbols

α_s	thermal expansion coefficient of substrate
α_c	thermal expansion coefficient of the repair laminate for either the axial or circumferential directions
c	crack length
D	original external diameter
D_b	original external branch, tee, nozzle diameter
d	diameter (or diameter of the equivalent circle) of the through-wall defect
ΔT	difference between operation and installation temperatures
E_c	tensile modulus of the composite laminate in the circumferential direction
E_a	tensile modulus of the composite laminate in axial direction
E_{ac}	combined tensile modulus $\sqrt{E_a E_c}$
E_s	tensile modulus of substrate
ε_c	circumferential design strain
ε_{c0}	allowable circumferential strain

ε_a	axial design strain
ε_{a0}	allowable axial strain
σ_{lt}	lower confidence limit of the long-term strain determined by performance testing
ε_t	thermal strain
ε_{short}	short-term failure strain of the composite laminate
F_{ax}	applied axial load
F_{eq}	equivalent axial load
F_{sh}	applied shear load
f_c	service factor for cyclic fatigue
f_D	degradation factor for the long-term performance of repairs to through-wall defects
f_{leak}	service factor for repairs to through-wall defects
f_{perf}	service factor for performance data
$f_{th,overlay}$	repair thickness increase factor for reduced available overlap length
$f_{th,stress}$	repair thickness increase factor for piping system or vessel component
f_{T1}	temperature de-rating factor for composite laminate allowable strains
f_{T2}	temperature de-rating factor for through-wall defect repair design
ϕ	angle subtended by axial slot
G	shear modulus of the composite laminate γ toughness parameter (energy release rate) for the composite laminate-steel interface
γ_{soilg}	specific weight of soil
h	burial depth
I	second moment of area
l	total axial length of repair
$l_{available}$	available landing area (axial extent) of undamaged substrate
l_{over}	axial extent of design thickness of repair
l_{defect}	axial length of defect
l_{taper}	axial length of taper
N	number of cycles
M_{ax}	applied axial moment
M_{to}	applied torsional moment
n	number of wraps or layers or repair laminate
p	required design internal pressure

p_{after}	internal pressure after repair system is applied
p_e	external design pressure
p_{eq}	equivalent design pressure
$p_{\text{ext,soil}}$	external soil pressure
p_{live}	internal pressure within the substrate during application of the repair
p_{min}	minimum (internal pressure) load (or stress) of the load cycle
p_{max}	maximum (internal pressure) load (or stress) of the load cycle
p_{mthp}	medium-term hydrostatic test pressure
p_s	maximum allowable working pressure (MAWP)
p_{sthp}	short-term hydrostatic test pressure
p_0	initial test pressure
p_1	fixed linear increase in test pressure
q	tensile stress
R_c	cyclic loading severity, defined as: $R_c = \frac{p_{\text{min}}}{p_{\text{max}}}$
s	allowable stress of the substrate material
s_a	measured yield stress of substrate or mill certification yield stress
T_d	required design temperature
T_g	glass transition temperature
T_m	maximum operating temperature of repair system
T_{amb}	ambient (qualification) test temperature
T_{test}	qualification test temperature
t	original wall thickness of substrate
t_{lifetime}	repair design lifetime
t_{layer}	thickness of an individual wrap or layer of repair laminate
t_b	wall thickness of branch, tee
t_f	wall thickness of flange
t_{design}	design thickness of repair laminate
t_{min}	minimum thickness of repair laminate
t_s	minimum remaining substrate wall thickness

τ	lap shear strength
ν	Poisson's ratio for the repair laminate
w	(axial) width of circumferential slot defect

4.2 Abbreviated terms

ASME	American Society of Mechanical Engineers
ASTM	American Society for Testing and Materials
API	American Petroleum Institute
AWWA	American Water Works Association
BS (BSI)	British Standards Institute
CFRP	carbon fibre-reinforced plastic
COSHH	regulations for control of substances hazardous to health
CSWIP	certification scheme for welding inspection personnel
DSC	differential scanning calorimetry
FRP	fibre-reinforced plastic
GRP	glass-reinforced plastic
HDT	heat distortion temperature
MAWP	maximum allowable working pressure
MSDS	materials safety data sheets
NDT	non-destructive testing
OSHA	Occupational Safety and Health Act
PCC	Post-Construction Committee
SMYS	specified minimum yield strength

5 Applications

The qualification and design, installation, testing and inspection procedures for composite repair systems in this document cover situations involving the repair of damage commonly encountered in oil, gas, utility pipework systems and vessels. The procedures are also applicable to the repair of pipelines, caissons and storage tanks with appropriate consideration.

Procedures in this document cover the repair of metallic and GRP pipework, pipework components, pipelines originally designed in accordance with a variety of standards, including ISO 15649, ISO 13623, ISO 14692, ASME B31.1, ASME B31.3, ASME B31.4, ASME B31.8 and BS 8010.

This document is not a defect assessment standard. Within this document, no statements are made regarding whether a specific defect is acceptable or unacceptable for repair. The document assumes that a defect assessment has already been performed to, for example ASME B31G or API RP 579. The starting point for this document is that a decision has been taken to repair a given defect with a composite repair system and the output from the defect assessment, e.g. MAWP or minimum remaining

wall thickness is used as input for the repair design. This document is concerned with the subsequent activities of repair qualification, design, installation and inspection.

Repair systems are applied to restore structural integrity. The following repair situations are addressed:

- external corrosion, where the defect is or is not through-wall. In this case, the application of a repair system will usually arrest further deterioration;
- external damage such as dents, gouges and fretting (at supports);
- internal corrosion, erosion, where the defect is or is not through-wall. In this case, corrosion and/or erosion can continue after application of a repair system, and therefore the design of the repair system shall take this into account, i.e. the size of the defect at the end of the required design life of the repair should be taken as the size of the defect when designing the repair;
- crack like defects, where the defect is or is not through wall. It is a requirement that the length of the crack is known and will not increase during the lifetime of the repair. For through wall cracks, the crack should be modelled as a Type B defect, either a circumferential or axial slot (depending on the crack orientation). For non-through wall cracks, the crack should be modelled as Type A defect, see 7.5.4;
- strengthening and/or stiffening in local areas.

As a general guide, Table 1 summarizes the types of defect that can be repaired using repair systems.

Table 1 — Guide to generic defect types

Type of defect	Applicability of repair system (metal pipes)	Applicability of repair system (GRP pipes)
General wall thinning	Y	Y
Local wall thinning	Y	Y
Pitting	Y	Y
Gouges/Dents	R	R
Blisters	Y	R
Laminations	Y	R
Circumferential cracks	Y	R
Longitudinal cracks	R	R
Through-wall penetration	Y	R
<p>Y Implies generally appropriate.</p> <p>R Implies can be used, but requires extra consideration, i.e. will the composite repair reduce locally the stresses acting on the defect. For the case of gouges/dents or cracks, it will be required to assess whether application of the repair will stop future crack growth or whether a conservative assumption about the ultimate length of the crack is required. If either assessment is negative, then application of a composite repair is not appropriate.</p>		

Services that are covered within the scope of this document include those normally found in an oil and gas production or processing installation. These include the following:

- utility fluid, diesel, seawater, air;
- chemicals (liquids);
- production fluids, including liquid hydrocarbons, gaseous hydrocarbons and gas condensates.

The upper temperature limit is defined in 7.5.3.

The lower temperature limit is dependent on the type of repair laminate being used. This limit is determined by the design requirements presented in 7.5.3.

The upper pressure limit is a function of defect type (internal, external, or through-wall), defect dimensions (depth and extent), pipe diameter, design temperature and repair design lifetime. Therefore, a unique number cannot be quoted but rather the limit is derived for a given set of conditions by calculations in accordance with this document using the qualification test data.

The lower pressure limit, e.g. vacuum conditions, is determined by the design requirements presented in [7.5.9.7](#).

The composite materials constituting the repair laminate considered within this document are typically those with aramid (AFRP), carbon (CFRP), glass (GRP), or polyester (or similar material) fibre reinforcement in a polyester, vinyl ester, epoxy, or polyurethane polymer matrix. Other fibre and matrix types are also permissible once qualified.

The pipework and vessel substrates considered within the standard include carbon steel, 6 moly steel, stainless steel, duplex steel, super duplex steel, GRP, Cunifer, aluminium, galvanised steel and titanium. Careful consideration is required before repair of GRP lines because the damage in the pipe may be more extensive than is visible on the surface and may affect a longer length of the pipe than is immediately obvious; advice of the GRP pipe manufacture and repair system supplier shall be sought before a repair is installed.

6 Summary of key issues

The key issues to be considered by the owner to ensure that a repair system complies with the requirements of this document are specified in the relevant clauses of this document.

The repair system is defined as the combination of the following elements and procedures:

- a) substrate, (component, e.g. pipe, pipeline tank and vessel outer surface);
- b) surface preparation;
- c) application of filler material;
- d) application of primer layer;
- e) application of repair laminate;
- f) curing procedure.

This document does not provide guidance on when to use a repair system. It starts from the point that a decision to use a repair system has already been taken and gives guidance on how to use repair systems effectively covering testing, design, installer training, installation and through to maintenance of a repair in service.

There are six key areas of the repair process that shall be considered.

Repair system qualification

The owner shall confirm the repair system proposed has been tested in accordance with the requirements of this document (see [Clause 7](#)). This would typically require the supplier to submit test reports or to provide third-party verification that testing has been completed.

Qualification testing is specific to a particular pipe material and method of surface preparation for that material. The owner shall confirm that testing has been completed for the pipe material of interest and the method of surface preparation being considered.

Enquiry stage

All relevant data, e.g. design conditions, corrosion mechanisms, inspection data and surface preparation limitations, shall be passed from the owner to the repair system supplier (see [7.4](#)). Full details of design

temperatures and pressures shall be provided. Upset conditions shall be considered, for example, if steaming of the line is expected, then this shall be noted.

Any limitations on working conditions shall be identified and supplied to the repair system installer/supplier through completion of the Design data sheet form (see [Annex A](#)). Risk assessment and an overview of site conditions should be supplied by the owner.

The status of the pipework during repair application, e.g. live, no pressure but full and empty, shall be defined and passed on from the owner to the repair system supplier. Details of the expected surface temperature and local humidity shall also be provided.

A photographic record of the defect prior to repair design/application should be kept by the owner.

Design of repair

The correct design procedure shall be followed as defined in [Figure 1](#).

When designed in accordance with this document, repair systems can provide strengthening of lines to relatively high pressures for Type A defects but can only be used at lower pressures for Type B defects. The limits for Type B defects are strongly affected by the size of defect assumed.

The selection of the generic through-wall defect and size for design, i.e. the selection of the correct dimension, may not simply be the size of the actual defect but rather may be either the dimension of the unprepared surface area neighbouring the defect or if filler is used over the defect, the dimension of the defect is the surface area of filler (see [7.5.7](#)).

Repairs to lines suffering internal corrosion or erosion should consider the defect size expected at the end of the repair service life. The repairs would generally be less resistant to erosion than a metal pipe and repair life would normally be restricted to the point that the defect goes through-wall.

The repair system supplier shall demonstrate how the repair system will satisfy the design requirements of this document regarding temperature where the pipe has an elevated design temperature but generally operates at ambient or has an elevated design temperature but the repair is installed at ambient (see [7.5.3](#)).

Installer training

Correct installation will ultimately determine successful performance of a repair as defined in [Table 14](#).

Repair installers shall have been trained in the application of the specific repair system in use.

The owner shall confirm that repair installers have been trained in compliance with the requirements of this document. The repair system supplier shall demonstrate competence of the installers via evidence of training and experience (see [Annex I](#)).

Installation of repair

In terms of the performance of the repair system, the adhesion of the repair to the substrate is the key technical issue. The surface preparation procedure should be the same as that qualified by testing and assumed in the design. The pipe surface shall be dry and at a temperature above the dew point or otherwise in compliance with the conditions validated by repair qualification testing.

The actual defect size should be confirmed as being within the limits assumed in the design (e.g. physical dimension, unprepared surface area or surface area of filler).

QA measurements shall be recorded (as per the repair system supplier's method statement), as the repair is being applied (see [Table 14](#)). The repair shall be fully cured before the pressure is brought back to normal operating conditions. The repair system supplier shall provide details on how to assess the cure status of the repair laminate (see [Table 14](#)).

A photographic record of the repair application should be kept by the repair system supplier.

The completed QA measurements and photographs (if available) shall be submitted to and retained by the owner and the repair system supplier shortly after installation is completed.

The ends of the repairs, where they extend on to base metal, as a minimum should be painted over to prevent corrosion to the pipe at this location.

Inspection and maintenance of repair

If considered necessary, the repair should be inspected on a regular basis to ensure the integrity of the repair and that it is operating within the assumptions used in the design of repair (i.e. the defect size is less than assumed in design) (see [Clause 9](#)). It may be appropriate to complete a baseline inspection immediately after application against which future inspections can be compared and changes identified.

At the end of the repair design lifetime, either the spool onto which the repair is situated should be removed, the repair removed, or the repair design lifetime revalidated (see [9.5](#)).

7 Qualification and design

7.1 Repair feasibility assessment

The following factors shall be considered by the owner and repair system supplier when assessing the feasibility of designing and installing a repair system:

- assessment of the nature and location of the defects;
- design and operating conditions for the substrate and contents (including pressure, temperature, sizes and combinations thereof);
- repair design lifetime (see [7.3](#));
- geometry of the substrate being repaired;
- hazards associated with system service;
- availability of personnel with the necessary skills;
- ease with which it is practicable to execute surface preparation operations;
- performance under upset and major incident situations, including impact, abrasion, fire, explosion, collision and environmental loading;
- operational measures, including (if relevant) permits, gas testing and fire protection requirements to ensure safety in the vicinity of the repair area;
- failure modes;
- inspectability (both visual and non-destructive) and maintenance of the repair;
- repair system materials.

For clarification, the assessment is not intended as a means to predetermine that the repair system is the appropriate strategy or remedial action, but rather to assess the feasibility associated with applying the repair system.

The information and data describing any hazards shall be included in the method statement ([8.2](#)) to be used on site.

Since the application of these repair systems typically changes the mode of failure from rupture of the substrate to a leak, the consequences of failure will therefore be reduced.

The objective of the assessment shall be to establish the class of the repair (7.2), which determines the detail of the design method (7.5) to be carried out, together with the requirements for supporting documentation. This also determines the design margin or factor of safety to be used in the design.

Guidance on performing the assessment can be obtained from Reference [36].

7.2 Repair class

Each repair shall be allocated to a particular class as defined in Table 2.

Class 1 repairs cover design pressures up to 2 MPa (20 bar), design temperatures up to 40 °C and are appropriate for the majority of the utility service systems. This class is intended for those systems that do not relate directly to personnel safety or safety-critical systems.

Class 2 repairs cover design pressures up to 2 MPa (20 bar) and design temperatures up to 100 °C but exclude hydrocarbons. This class is appropriate for those systems that have specific safety-related functions.

Class 3 repairs cover all fluid types and pressures up to the qualified upper pressure limit. This class is appropriate for systems transporting produced fluids.

Applications in which the service conditions are more onerous or not included in the above shall be designated as Class 3.

Table 2 — Repair class

Repair class	Typical service	Design pressure	Design temperature
Class 1	Low specification duties, e.g. static head, drains, cooling medium and sea (service) water	<2 MPa	<40 °C
Class 2	Fire water/deluge systems	<2 MPa	<100 °C
Class 3	Produced water and hydrocarbons, flammable fluids, gas systems Class 3 also covers operating conditions more onerous than described above.	Limited to repairs designed in compliance with this document and of a thickness equivalent to <D/12	Defined in 7.5.3

The qualified upper pressure limit is a function of defect type (internal, external or through-wall), defect dimensions (depth and extent), pipe diameter, design temperature and repair design lifetime. Therefore, a unique number cannot be quoted but rather the limit is derived for a given set of conditions by calculations in accordance with this document using the qualification test data from either Annex C for Type A defects and Annex D for Type B defects.

7.3 Repair design lifetime

The repair design lifetime (in years) of the repair system shall be defined by the owner in the repair data sheet (Annex A). It may be limited by the defect type and service conditions, e.g. internal corrosion.

The minimum design lifetime of the repair shall be two years.

Short design lifetimes (two years) may be appropriate to those situations where the repair is required to survive until the next shutdown.

Long design lifetimes (up to 20 years) may be appropriate to those situations where the repair is required to reinstate the substrate to its original design lifetime or to extend its design life for a specified period.

The repair design lifetime is the maximum application lifetime of the repair. The actual application or service lifetime, often termed the defined lifetime, maybe less than the repair design lifetime.

Once the repair design lifetime has expired, the owner shall either remove or revalidate the repair system as described in [9.5](#).

7.4 Required data

7.4.1 Background

The following data shall be supplied for each repair application. The detail to which these requirements are fulfilled is determined by the output of the repair feasibility assessment. Original equipment design data, maintenance and operational histories shall be provided by the owner and material qualification data shall be provided by the repair system supplier. The availability of relevant data shall feature as part of the repair feasibility assessment.

7.4.2 Original equipment design data

Original equipment design data is required, consisting of the following:

- a) piping line lists or other documentation showing process design conditions and a description of the piping class, including material specification, wall thickness, and pressure and temperature ratings;
- b) piping isometric drawings and, if appropriate, the output of a piping flexibility calculation;
- c) specification of all operating mechanical loads not included in the above, including upset conditions;
- d) original design calculations;
- e) regulatory requirements, e.g. fire performance.

7.4.3 Maintenance and operational histories

Maintenance and operational histories are required, consisting of the following:

- a) documentation of any changes in service conditions, including pressure, temperature, internal fluids and corrosion rate;
- b) past service conditions;
- c) summary of all alterations and past repairs local to the substrate of concern;
- d) inspection reports detailing the nature and extent of damage to be repaired.

7.4.4 Service condition data

Service condition data are required, consisting of the following:

- a) repair design lifetime requirements/expectations;
- b) required design and operating pressures (internal and external)/temperatures;
- c) expected future service conditions;
- d) if applicable, MAWP as calculated according to the requirements of ASME B31G, API 579, BS 7910 or other applicable standard. This shall be carried out taking into account the current position and any possible further degradation in the future.

An example of a design data sheet is presented in [Annex A](#).

7.4.5 Repair system qualification data

The documentation and qualification data related to repair systems that shall be provided for the repair system are shown in [Table 3](#).

Details of the qualification data to be provided are given in [Annex B](#).

Table 3 — Documentation and data requirements

Documentation requirement	Class 1	Class 2	Class 3
Material documentation and data	✓	✓	✓
Surface preparation documentation	✓	✓	✓
Short-term test data	✓	✓	✓
Long-term test data		✓	✓

Clarification of the terms used in [Table 3](#) is as follows:

a) Material documentation and data

This shall include a statement of the resins and reinforcements used and any standards to which they are supplied. Basic data on material compatibility with the working environment shall also be available. It shall be ensured that any chemical interaction between the resin (and associated curing agents) and substrate will not cause further degradation of the substrate. Also, attention shall be given to CFRP laminates and the potential for bimetallic (galvanic) corrosion of the substrate.

b) Surface preparation

The durability of a bonded assembly under applied load is determined to a large extent by the quality of the surface preparation used. Details of the surface preparation procedure and how it is to be implemented shall be provided as used in the qualification tests.

c) Short-term test data

These shall include tensile strength and modulus in both the hoop and axial directions and the strength of the (adhesive) bond between the repair laminate and the substrate.

d) Long-term lap shear durability test data

These shall include the strength of the adhesive bond between the repair laminate and substrate, and optionally the ultimate tensile strain of the repair laminate. Long-term is defined as greater than or equal to 1 000 h where the sample has been exposed to a water environment and a temperature greater than or equal to the design temperature. Above a temperature of 100 °C, the environment can be dry.

[Table 4](#) lists the data required to comply with Class 3 requirements. [Annex B](#) contains the full details of the qualification data requirements.

Table 4 — Qualification test requirements

	Material property	Test method
Mechanical properties	Young's modulus	ISO 527-1, ISO 527-4 (or ASTM D3039)
	Poisson's ratio	ISO 527-1, ISO 527-4 (or ASTM D3039)
	Shear modulus	ASTM D5379
	Thermal expansion coefficient	ISO 11359-2 (or ASTM D696)
	Glass transition temperature of resin or heat distortion temperature of resin cured at relevant temperatures	ISO 11357-2 (or ISO 75-3, ASTM D6604, ASTM E1640, ASTM E831), ASTM E2092
	Barcol or Shore hardness	ISO 868 or EN 59 (or ASTM D2583)
Adhesion strength	Lap shear	EN 1465 (or ASTM D3165)
Performance data	Long-term strength (optional)	Annex E
	Energy release rate (optional)	Annex D
	Short-term pipe spool survival test	Annex C
	Impact survival test	Annex F
	Degradation factor (optional)	Annex G

7.5 Design methodology

7.5.1 Overview

There are two design cases.

a) Defect type A (non through-wall defect) design case

The defect is within the substrate, not through-wall and not expected to become through-wall within the repair design lifetime of the repair system, requiring structural reinforcement only. One of the following three design methods shall be used to determine the repair laminate thickness, t_{design} :

- 1) include allowance for the substrate (see [7.5.4](#));
- 2) exclude allowance for the substrate (see [7.5.5](#));
- 3) long-term performance test data (see [7.5.6](#)).

b) Defect type B (through-wall defect) design case

The substrate requires structural reinforcement and sealing of through-wall defects (leaks). For substrates with active internal corrosion, the repair laminate shall be designed on the assumption that a through-wall defect will occur if the remaining wall thickness at the end of service life is expected to be less than 1 mm. Both of the following design methods shall be used:

- 1) the design method in [7.5.7](#);
- 2) the design method for the defect type A design case.

The greater repair thickness from the defect type A design case or the design method in [7.5.7](#) shall be taken as the repair laminate thickness, t_{design} .

[7.5.9](#) and [7.5.13](#) shall be considered for each design case and applied where appropriate, with the largest thickness being taken as the repair laminate thickness, t_{design} .

The flowchart presented in [Figure 1](#) provides an overview of the above described design process. Further informative guidance on the repair design process is given in [Annex K](#). Within [Annex K](#), two worked examples (for a Type A and Type B defect) are provided.

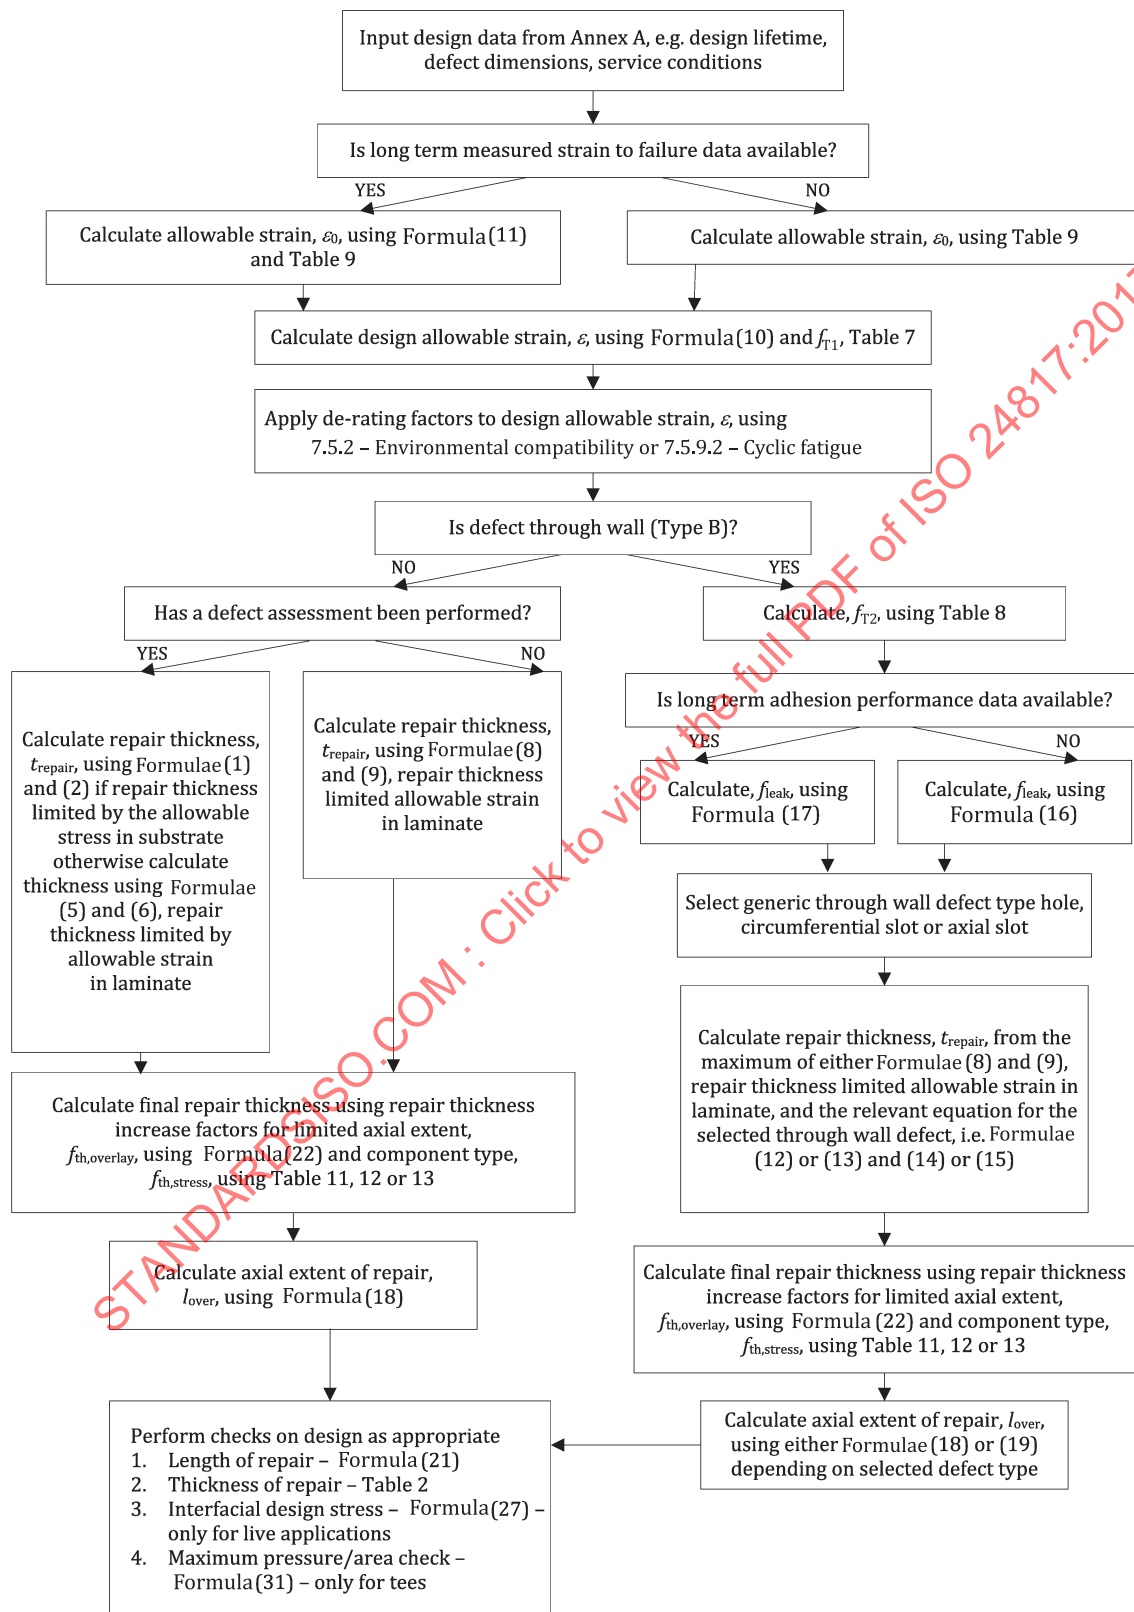


Figure 1 — Flowchart summarizing repair system design process

7.5.2 Environmental compatibility

The suitability for use of the repair system in the service environment shall be based on the following considerations. The service environment is the environment that contacts the repair laminate. It may be either the external or internal environment.

The qualification of the repair system (7.4.5) demonstrates that the repair system is compatible with aqueous (wet) and hydrocarbon environments at the qualification test temperature. In general, thermoset resins are compatible with a wide range of environments, but consideration shall be given when the environment is strongly acidic ($\text{pH} < 3,5$), strongly alkaline ($\text{pH} > 11$), highly saline or is a strong solvent, e.g. methanol, glycol, benzene and toluene in concentration greater than 25 %.

Resistance to UV degradation and weathering (where appropriate) shall be provided by data from the resin supplier.

When the environmental compatibility of the repair system is unknown, then the repair system supplier shall provide one of the following to demonstrate compatibility:

- environmental compatibility data or experience of previous applications from the resin supplier, demonstrating that the environment is no more aggressive than aqueous or hydrocarbon environments at the design temperature;
- if no compatibility data from the resin supplier is available, then specific environmental testing is required. One of the following test procedures, ISO 10952, ASTM D543, ASTM C581, ASTM D3681 or equivalent, comparing the exposure of the specific environment and aqueous environment to the repair laminate at the design temperature shall be performed. The repair system shall be considered compatible to the specific environment if the test results from the specific environment are no worse than for the aqueous environment.

When particulate erosion is the cause of the degradation process of the substrate and the repair laminate is in contact with the eroding medium, then the repair laminate can suffer material loss. The repair system supplier shall demonstrate the survival of the repair system for the specified repair design lifetime assuming a conservative estimate of the loss of laminate material. Without experimental data on the erosion rate, a maximum repair design lifetime of no more than two years is recommended. Alternatively, a metal plate can be placed over the affected area prior to application of the repair laminate to minimize material loss (of the laminate), wherein the design of the repair the dimensions of the plate are taken as the size of the defect.

When considering the repair to GRP pipes or vessels, the chemical interaction between both solvent used to clean the surface and also the uncured resin constituents of the repair material and the GRP material should be considered.

7.5.3 Design temperature effects

The thermal properties of the repair system shall satisfy the requirements given in Table 5. The value of T_g or HDT used shall be determined in Annex B for a repair system cured at a temperature no greater than the design temperature of the repair, T_d . The cure schedule (time and temperature profile) required to achieve this shall be specified. The temperature limit of a repair system shall be defined with reference to T_g unless the repair system does not show this transition in which case the temperature limit shall be defined with reference to HDT. Repairs that are applied to systems that are depressurised and drained may be heated (post-cured) to give the required value of T_g or HDT. The heating cycle used shall have been demonstrated to achieve the required value of T_g or HDT during qualification testing.

Table 5 — Thermal property requirements for repair systems

Repair class	Defect type A limit	Defect type B limit	
		Repair design lifetime ≤ 2 years	Repair design lifetime > 2 years
Class 1 and 2	$T_g \geq T_d + 20\text{ °C}$ $HDT \geq T_d + 15\text{ °C}$	$T_g \geq T_d + 20\text{ °C}$ $HDT \geq T_d + 15\text{ °C}$	
Class 3		$T_g \geq T_d + 20\text{ °C}$ $HDT \geq T_d + 15\text{ °C}$	$T_g \geq T_d + 30\text{ °C}$ $HDT \geq T_d + 20\text{ °C}$

Hardness can give an indication of cure and, where measured, shall be no less than 90 % of the minimum obtained from repair system qualification in accordance with [Table 4](#). Hardness alone shall not be relied upon to demonstrate cure for repair to Class 3 systems; reference shall also be made to the cure schedule.

For a repair system where the defect within the substrate is not through-wall, the temperature limit can be relaxed to T_g less 20 °C or HDT less 15 °C. T_g or HDT shall be measured in accordance with [Table 4](#). [Table 6](#) summarizes the upper temperature limit of the repair when cured to as specified in [Clause 7](#).

Table 6 — Service temperature limits for repair systems

	Defect type A limit T_m	Defect type B limit T_m	
		Repair design lifetime ≤ 2 years	Repair design lifetime > 2 years
Class 1 and 2	$T_g - 20\text{ °C}$	$T_g - 20\text{ °C}$	$T_g - 20\text{ °C}/HDT - 15\text{ °C}$
Class 3	$HDT - 15\text{ °C}$	$HDT - 15\text{ °C}$	$T_g - 30\text{ °C}/HDT - 20\text{ °C}$

The temperature de-rating factor, f_{T1} , to account for elevated design temperature application used in [Formula \(10\)](#) is given in [Table 7](#), where T_m is the upper temperature limit for the system (as defined in [Table 6](#)), in degree Celsius.

Table 7 — Temperature de-rating factor for composite laminate allowable strains, f_{T1}

Temperature factor; f_{T1}	$0,000\,062\,5(T_m - T_d)^2 + 0,001\,25(T_m - T_d) + 0,7$
------------------------------	---

The additional requirements for repairs to through-wall defects are qualified through performance testing. To allow for higher design temperatures than the qualification test temperature, [Table 8](#) defines the temperature de-rating factor, f_{T2} , that shall be applied to [Formula \(12\)](#) to [Formula \(15\)](#), where T_{amb} is the ambient test temperature, in degree Celsius and T_{test} is the qualification test temperature, in degree Celsius.

Table 8 — Temperature de-rating factor for through-wall defects (Type B defect) and performance test data, f_{T2}

Temperature factor; f_{T2}	$0,000\,062\,5[T_m - T_d - (T_{test} - T_{amb})]^2 + 0,001\,25[T_m - T_d - (T_{test} - T_{amb})] + 0,7$
------------------------------	---

The formulae presented in [Table 7](#) and [Table 8](#) are based on similar temperature de-rating factors as defined in EN 13121.

Where a repair will generally be operating at a lower temperature than T_d , then the T_g value associated with this lower operating temperature shall be checked and the relevant value of f_{T1} derived. The lower of the values of f_{T1} obtained shall be used in the design of the repair. In this case, it is assumed the repair system will cure to a satisfactory level when the temperature in the line increases. If this temperature increase is expected to be relatively fast (i.e. <30 min), then the repair system supplier shall be advised of this. The repair system supplier shall demonstrate this rate of heating is acceptable by test; otherwise, the repair shall be post-cured using external heating. Post-curing shall only be undertaken on pipes which are depressurised and drained.

7.5.4 Design based on substrate load sharing (defect type A)

Use of the design method in this subclause is appropriate if the contribution of the substrate is to be included in the calculation for load-carrying capability.

7.5.4.1 Limited by allowable stress in the substrate

[Formulae \(1\)](#) and [\(2\)](#) shall be used when it is assumed that the repair thickness is limited by the allowable stress in the substrate.

In the circumferential direction, the minimum repair laminate thickness, t_{\min} (expressed in millimetres), is given by [Formula \(1\)](#):

$$t_{\min,c} = \frac{D}{2s} \cdot \left(\frac{E_s}{E_c} \right) \cdot \left(p_{eq} + \frac{2\nu F_{eq}}{\pi D^2} - p_s \right) \quad (1)$$

In the axial direction, the minimum repair laminate thickness, t_{\min} (expressed in millimetres), is given by [Formula \(2\)](#):

$$t_{\min,a} = \frac{D}{2s} \cdot \left(\frac{E_s}{E_a} \right) \cdot \left(\frac{2F_{eq}}{\pi D^2} - \nu \frac{E_a}{E_c} p_{eq} - p_s \right) \quad (2)$$

where

E_a is the axial modulus of the repair laminate, expressed in megapascals;

E_c is the circumferential modulus of the repair laminate, expressed in megapascals;

E_s is the modulus of substrate, expressed in megapascals;

D is the original external diameter, expressed in millimetres;

F_{eq} is the equivalent axial load, expressed in newtons [see [Formula \(4\)](#)];

ν is the Poisson's ratio of the repair laminate (see [Annex B](#) for definition);

s is the allowable stress of the substrate material, expressed in megapascals;

p_{eq} is the equivalent internal pressure, expressed in megapascals [see [Formula \(3\)](#)];

p_s is the MAWP, expressed in megapascals, which is defined according to the relevant defect assessment code;

t_s is the minimum remaining substrate wall thickness, expressed in millimetres.

NOTE It is possible that when using [Formula \(2\)](#), that negative repair thickness values are calculated. This implies that the remaining wall thickness is sufficient to withstand the applied loads in the axial direction.

In [Formula \(2\)](#), the contribution of F_{eq} shall be taken as positive.

p_{eq} and F_{eq} are defined as:

$$p_{eq} = p \left[1 + \frac{16}{(\pi D^2 p)^2} \left(F_{sh} + \frac{2}{D} M_{to} \right)^2 \right] \quad \text{for } p \geq \frac{4}{\pi D^2} \left(F_{sh} + \frac{2}{D} M_{to} \right)$$

$$p_{eq} = p + \frac{4}{\pi D^2} \left(F_{sh} + \frac{2}{D} M_{to} \right) \quad \text{for } p < \frac{4}{\pi D^2} \left(F_{sh} + \frac{2}{D} M_{to} \right) \quad (3)$$

$$F_{eq} = \frac{\pi}{4} p D^2 + \sqrt{F_{ax}^2 + 4F_{sh}^2} + \frac{4}{D} \sqrt{M_{ax}^2 + M_{to}^2} \quad (4)$$

where

p is the required internal design pressure, expressed in megapascals;

F_{sh} is the applied shear load, expressed in newtons;

M_{to} is the applied torsional moment, expressed in newton millimetres;

F_{ax} is the applied axial load, expressed in newtons;

M_{ax} is the applied axial moment, expressed in newton millimetres.

The design repair thickness, t_{design} (expressed in millimetres), shall be the maximum value of $t_{min,c}$ and $t_{min,a}$ determined from [Formulae \(1\)](#) and [\(2\)](#).

If the purpose of the repair system is to strengthen an undamaged section to carry additional bending or other axial loads, the value of F_{eq} shall be taken to be the increased total axial load requirement and the value of p_s shall be the MAWP after the defect has been assessed.

[Formulae \(1\)](#) and [\(2\)](#) are valid for repair thickness $t_{design} < \frac{D}{12}$.

The assumption made in deriving [Formulae \(1\)](#) and [\(2\)](#) is that the substrate is elastic.

7.5.4.2 Limited by allowable strain in the repair laminate

[Formulae \(5\)](#) and [\(6\)](#) shall be used when it is assumed that the repair thickness is limited by the allowable strain of the repair laminate (see [7.5.5](#)). In the circumferential direction, the minimum repair laminate thickness, t_{min} (expressed in millimetres) is given by [Formula \(5\)](#):

$$\varepsilon_c = \frac{1}{E_c t_{min}} \left(\frac{p_{eq} D}{2} + v \frac{F_{eq}}{\pi D} \right) - \frac{p_s D}{2 E_c t_{min}} - \frac{p_{live} D}{2 (E_c t_{min} + E_s t_s)} \quad (5)$$

In the axial direction, the minimum repair laminate thickness, t_{min} (expressed in millimetres), is given by [Formula \(6\)](#):

$$t_{min,a} = \frac{1}{\varepsilon_a} \left(\frac{F_{eq}}{\pi D} \frac{1}{E_a} + \frac{p_{eq} D}{2} \frac{v}{E_c} \right) \quad (6)$$

where

p_{live} is the internal pressure during repair installation, expressed in megapascals;

ε_c is the allowable repair laminate circumferential strain, expressed in millimetres per millimetre, as derived in [7.5.5](#) or [7.5.6](#);

ε_a is the allowable repair laminate axial strain, expressed in millimetres per millimetre, as derived in [7.5.5](#) or [7.5.6](#).

If the repair is applied at zero internal pressure, i.e. $p_{\text{live}} = 0$, and axial loads can be neglected, i.e. buried pipelines, then [Formula \(5\)](#) can be rearranged to give:

$$t_{\min} = \frac{D}{2\varepsilon_c E_c} (p_{\text{eq}} - p_s) \quad (7)$$

The design repair thickness, t_{design} , shall be taken as the maximum value determined from either [Formula \(5\)](#) or [Formula \(6\)](#).

[Formulae \(5\) to \(7\)](#) are valid for repair thickness $t_{\text{design}} < \frac{D}{12}$.

The assumptions made in deriving [Formulae \(5\) to \(7\)](#) are that the substrate is elastic and only contributes to the load-sharing up to the allowable stress (of the substrate).

7.5.5 Design based on repair laminate allowable strains (defect type A)

Use of the design method in this subclause is appropriate if the contribution of the substrate is to be ignored in the calculation for load-carrying capability and if short-term material properties are to be used.

In the circumferential direction, the minimum repair laminate thickness, t_{\min} (expressed in millimetres), due to internal pressure, bending, and axial thrust, is given by:

$$t_{\min,c} = \frac{1}{\varepsilon_c} \left(\frac{p_{\text{eq}} D}{2} \frac{1}{E_c} + \frac{F_{\text{eq}}}{\pi D} \frac{\nu}{E_c} \right) \quad (8)$$

In [Formula \(8\)](#), the contribution of F_{eq} shall be taken as positive.

In the axial direction, the minimum repair laminate thickness, t_{\min} (expressed in millimetres), due to internal pressure, bending and axial thrust, is given by:

$$t_{\min,a} = \frac{1}{\varepsilon_a} \left(\frac{F_{\text{eq}}}{\pi D} \frac{1}{E_a} - \frac{p_{\text{eq}} D}{2} \frac{\nu}{E_c} \right) \quad (9)$$

where

E_a is the axial modulus of the repair laminate, expressed in megapascals;

E_c is the circumferential modulus of the repair laminate, expressed in megapascals;

D is the original external diameter, expressed in millimetres;

F_{eq} is the equivalent axial load, expressed in newtons [see [Formula \(4\)](#)];

p_{eq} is the equivalent internal pressure, expressed in megapascals [see [Formula \(3\)](#)];

ν is the Poisson's ratio of the repair laminate (see [Annex B](#) for definition);

ε_a is the allowable repair laminate axial strain, expressed in millimetres per millimetre;

ε_c is the allowable repair laminate circumferential strain, expressed in millimetres per millimetre.

In [Formula \(9\)](#), the contribution of F_{eq} shall be taken as positive.

The design repair thickness, t_{design} , shall be the maximum value of $t_{\min,c}$ and $t_{\min,a}$ determined from [Formulae \(8\) and \(9\)](#).

[Formulae \(8\) and \(9\)](#) are valid for repair thickness $t_{\text{design}} < \frac{D}{12}$.

For occasional loads (short-duration loads), Class 1 minimum repair design lifetime (two years) strains shall be used; see [Table 9](#).

The allowable strains presented in [Table 9](#) shall only be used if the short-term strain to failure of the repair laminate is greater than 0,01; otherwise, performance data from [7.5.6](#) shall be used. The short-term strain to failure can be derived from the test carried out to determine the tensile properties of the laminate ([Table 4](#)).

The thermal expansion coefficient for a repair laminate is different from that of the substrate, resulting in the generation of thermal stresses within the repair laminate when the design temperature is different from the installation temperature. This effect shall be considered in the design assessment by subtracting the thermally induced strains from the allowable strains. The temperature factor, f_{T1} , shall be applied to the allowable strain before subtraction. The allowable repair laminate thermal strains in the circumferential and axial directions, ε_c and ε_a , shall be calculated by:

$$\begin{aligned}\varepsilon_c &= f_{T1}\varepsilon_{c0} - \left| \Delta T (\alpha_s - \alpha_c) \right| \\ \varepsilon_a &= f_{T1}\varepsilon_{a0} - \left| \Delta T (\alpha_s - \alpha_a) \right|\end{aligned}\quad (10)$$

where

- ε_{a0} is the allowable repair laminate axial strain [no temperature effect (see [Table 9](#))], expressed in millimetres per millimetre;
- ε_{c0} is the allowable repair laminate circumferential strain [no temperature effect (see [Table 9](#))], expressed in millimetres per millimetre;
- f_{T1} is the temperature de-rating factor (see [Table 7](#));
- α_a is the repair laminate thermal expansion coefficient, axial direction, expressed in millimetres per millimetre degree Celsius;
- α_c is the repair laminate thermal expansion coefficient, circumferential direction, expressed in millimetres per millimetre degree Celsius;
- α_s is the substrate thermal expansion coefficient, expressed in millimetres per millimetre degree Celsius;
- ΔT is the difference between design and installation temperatures, expressed in degree Celsius.

Table 9 — Allowable strains for composite laminates as a function of repair design lifetime

Modulus	Allowable strain Class 1	Allowable strain Class 2	Allowable strain Class 3
For $E_a > 0,5 E_c$			
— ε_{c0}	$0,004\,214 \times 10^{-0,011\,35 t_{\text{lifetime}}}$	$0,003\,634 \times 10^{-0,008\,13 t_{\text{lifetime}}}$	$0,003\,061 \times 10^{-0,004\,4 t_{\text{lifetime}}}$
— ε_{a0}	$0,004\,214 \times 10^{-0,011\,35 t_{\text{lifetime}}}$	$0,003\,634 \times 10^{-0,008\,13 t_{\text{lifetime}}}$	$0,003\,061 \times 10^{-0,004\,4 t_{\text{lifetime}}}$
For $E_a < 0,5 E_c$			
— ε_{c0}	$0,004\,214 \times 10^{-0,011\,35 t_{\text{lifetime}}}$	$0,003\,634 \times 10^{-0,008\,13 t_{\text{lifetime}}}$	$0,003\,061 \times 10^{-0,004\,4 t_{\text{lifetime}}}$
— ε_{a0}	$0,002\,768 \times 10^{-0,022\,1 t_{\text{lifetime}}}$	0,001	0,001

The values in [Table 9](#) include a service factor for safety equivalent to 0,67.

7.5.6 Design based on repair-allowable stresses determined by performance testing (defect type A)

Use of the design method in this subclause is appropriate if performance-based test data are available.

[Annex E](#) provides three methods for the determination of long-term failure strain of the repair laminate.

The allowable repair laminate circumferential strain, ε_c , (expressed in millimetres per millimetre) is given by [Formula \(11\)](#):

$$\varepsilon_c = f_{\text{perf}} f_{T2} \varepsilon_{\text{lt}} \quad (11)$$

where

ε_{lt} is the lower confidence limit of the long-term strain, expressed in millimetres per millimetre (see [Annex E](#));

f_{perf} is the service de-rating factor (see [Table 10](#));

f_{T2} is the temperature de-rating factor (see [Table 8](#)).

If allowance for the substrate is not to be included, then [Formula \(8\)](#) shall be used to calculate the minimum repair thickness in the circumferential direction.

If allowance for the substrate is to be included, then [Formula \(5\)](#) shall be used to calculate the minimum repair thickness in the circumferential direction.

Table 10 — Service factor, f_{perf} , for performance data of repair systems

Service factor	Class 1	Class 2	Class 3
1 000 h data	$0,878 \times 10^{-0,012 2 t_{\text{lifetime}}}$	$0,692 \times 10^{-0,007 t_{\text{lifetime}}}$	$0,612 \times 10^{-0,004 3 t_{\text{lifetime}}}$
Design life data	$1,045 5 \times 10^{-0,009 65 t_{\text{lifetime}}}$	$0,873 \times 10^{-0,005 75 t_{\text{lifetime}}}$	$0,76 \times 10^{-0,002 73 t_{\text{lifetime}}}$

7.5.7 Design of repairs for through-wall defects (defect type B)

A defect within a substrate shall be considered through-wall if the wall thickness at any point of the affected area is determined to be less than 1 mm at the end of its life.

Use of the design method in this subclause is appropriate if the defect within the substrate is through-wall or deemed to become through-wall at the end of its life. The requirements of this subclause are in addition to those described in [7.5.4](#), [7.5.5](#) or [7.5.6](#).

The dimension of the through-wall defect to be used in the design shall be based on the estimated size of the defect at the end of the required design life of the repair system.

In some circumstances, it may not be possible to prepare the substrate completely adjacent to the repair. Often a protective metal plate is used to protect the damaged substrate during surface preparation, e.g. grit blasting. In these circumstances, the dimension of the defect shall be taken as the unprepared substrate surface area (including metal plate plus any fairing material).

Also, if filler material is used over the defect, e.g. if a repair is to encompass a flange, then the size of the defect shall be taken as the surface area of the pipework covered by the filler material.

For a circular or near-circular defect, the minimum thickness for a repair laminate, t_{\min} (expressed in millimetres), shall be calculated using [Formula \(12\)](#):

$$p = f_{T2} f_{\text{leak}} \sqrt{\left\{ \frac{0,001 \gamma_{\text{LCL}}}{\left(\frac{1-v^2}{E_{\text{ac}}} \right) \left\{ \frac{3}{512 t_{\min}^3} d^4 + \frac{1}{\pi} d \right\} + \frac{3}{64 G t_{\min}} d^2} \right\}} \quad (12)$$

where

E_{ac} is the combined tensile modulus $\sqrt{E_a E_c}$, expressed in megapascals;

G is the shear modulus of the repair laminate, expressed in megapascals;

p is the design internal pressure, expressed in megapascals;

v is the Poisson's ratio of the repair laminate (see [Annex B](#) for definition);

d is the diameter of defect, expressed in millimetres;

t_{\min} is the thickness of repair laminate, expressed in millimetres;

γ_{LCL} is the 95 % lower confidence limit of energy release rate, expressed in joules per square metre (see [Annex D](#));

f_{T2} is the temperature de-rating factor, see [Table 8](#);

f_{leak} is the service de-rating factor [see [Formula \(16\)](#)].

Plugging of the through-wall defect in the tests performed to determine the value of γ_{LCL} ([Annex D](#)) is not allowed.

[Formula \(12\)](#) is valid for defect sizes $d \leq \sqrt{6Dt}$ where

D is the substrate external diameter, expressed in millimetres;

t is the substrate wall thickness, expressed in millimetres.

For non-circular defects that have an aspect ratio < 5 , [Formula \(12\)](#) shall be used where the value of d (effective defect diameter) is selected such that it contains the defect.

For the case of cracks, it will be required to assess whether application of the repair will stop future crack growth or whether a conservative assumption about the ultimate length of the crack to be used in the design calculation is required.

For a circumferential slot type defect, the minimum thickness for a repair laminate, t_{\min} expressed in millimetres, is calculated using the smallest value of repair thickness calculated from both [Formula \(13\)](#) and [Formula \(14\)](#):

$$p = f_{T2} f_{\text{leak}} \left\{ \frac{0,001 \gamma_{\text{LCL}}}{\left(\frac{1 - \nu^2}{E_{\text{ac}}} \right) \left\{ \frac{1}{24 t_{\min}^3} w^4 + \frac{\pi}{4} w \right\} + \frac{3}{16 G t_{\min}} \left(\frac{4}{5} + \frac{\nu}{2} \right) w^2} \right\} \quad (13)$$

$$p = \frac{f_{T2} f_{\text{leak}}}{D} \sqrt{0,008 E_{\text{ac}} t_{\min} \gamma_{\text{LCL}}} \quad (14)$$

where w is the axial width of the slot, expressed in millimetres.

[Formulae \(13\)](#) and [\(14\)](#) shall be used to assess the repair thickness required where the defect to be repaired is a pinhole in a weld. The slot width selected shall be sufficient to include the full width of the weld and any fairing material used in the repair application procedure.

For an axial slot type defect having a circumferential width of the slot, $w = \phi D/2$ expressed in millimetres, the minimum thickness for a repair laminate, t_{\min} expressed in millimetres, is calculated using [Formula \(15\)](#):

$$p = f_{T2} f_{\text{leak}} \left\{ \frac{0,001 \gamma_{\text{LCL}}}{\left(\frac{1 - \nu^2}{E_{\text{ac}}} \right) \left[\frac{\pi D}{8} \phi + \frac{D^4}{384 t_{\min}^3} \phi^4 + \frac{D^4}{11520 t_{\min}^3} \left(\frac{E_{\text{ac}}}{4G} + 2 \right) \phi^6 \right]} \right\} \quad (15)$$

where the limit on the applicability of [Formula \(15\)](#) is given by $\phi < 1$, where ϕ is the angle subtended by the axial slot, expressed in radians.

It is recommended that the size of defect used in [Formulae \(12\)](#) to [\(15\)](#) should be at least 15 mm.

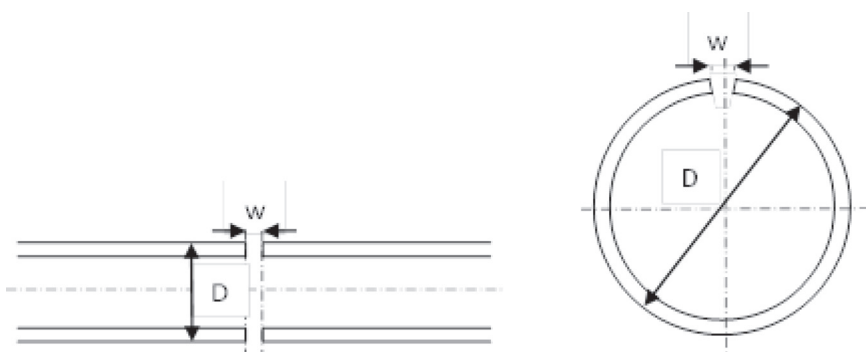


Figure 2 — Sketch showing details of circumferential and axial slots

The value of the service factor, f_{leak} , shall be set to:

Class 1	Class 2	Class 3	(16)
$f_{\text{leak}} = 0,83 \times 10^{-0,02088(t_{\text{lifetime}}-1)}$	$f_{\text{leak}} = 0,75 \times 10^{-0,01856(t_{\text{lifetime}}-1)}$	$f_{\text{leak}} = 0,666 \times 10^{-0,01584(t_{\text{lifetime}}-1)}$	

where t_{lifetime} is the repair design lifetime, expressed in years.

If long-term performance test data is available in accordance with [Annex E](#), then the service factor, f_{leak} , shall be calculated using:

Class 1	Class 2	Class 3	(17)
$f_{\text{leak}} = 0,83 f_D$	$f_{\text{leak}} = 0,75 f_D$	$f_{\text{leak}} = 0,666 f_D$	

where f_D is the degradation factor [defined in [Formula \(G.4\)](#)].

The design repair thickness, t_{design} , shall be the maximum value of the minimum repair thickness determined from one of [Formulae \(12\)](#), [\(13\)](#), [\(14\)](#) or [\(15\)](#), iteratively, and the design repair thickness derived in [7.5.4](#), [7.5.5](#) or [7.5.6](#).

7.5.8 Axial extent of repair

The design thickness of the repair laminate shall extend beyond the damaged region in the substrate by the larger of 50 mm or l_{over} expressed in millimetres, where l_{over} is given by [Formula \(18\)](#) or [Formula \(19\)](#):

For slot type defects:

$$l_{\text{over}} = 2\sqrt{Dt} \quad (18)$$

For circular type defects:

$$l_{\text{over}} = 4d \quad \text{where} \quad d < 0,5\sqrt{Dt} \quad (19)$$

where

d is the diameter of defect, expressed in millimetres;

D is the original external diameter of substrate, expressed in millimetres;

t is the thickness of substrate, expressed in millimetres.

If the equality in [Formula \(19\)](#) is not satisfied, then [Formula \(18\)](#) shall be used. [Annex H](#) presents a look-up table of axial extent of repair as a function of both diameter and defect size.

The total axial length of the repair, l (expressed in millimetres), is given by [Formula \(20\)](#):

$$l = 2l_{\text{over}} + l_{\text{defect}} + 2l_{\text{taper}} \quad (20)$$

The ends of the repair laminate shall be tapered if axial loads are present. These axial loads can result solely from end effects due to internal pressure or can result from system loads such as bending or thermal expansion. A minimum taper of approximately 5:1 is recommended.

To check that the axial extent of the repair, l_{over} , is sufficient to ensure that the applied axial load can be transferred from the substrate to the repair, [Formula \(21\)](#) shall be satisfied:

$$l_{\text{over}} > \frac{3E_a \varepsilon_a t_{\text{design}}}{\tau} \quad (21)$$

where

E_a is the axial modulus of repair laminate, expressed in megapascals;

ε_a is the allowable axial strain of repair system, expressed in millimetres per millimetre;

t_{design} is the minimum thickness of repair laminate for axial applied loads, expressed in millimetres [see either [Formula \(2\)](#), [Formula \(6\)](#) or [Formula \(9\)](#)];

τ is the lap shear strength, expressed in megapascals (see [Annex B](#)).

If the geometry of the section to be repaired is such that it is not possible to achieve the required axial extent of repair, l_{over} , plus the axial length of taper, l_{taper} , the following shall apply. The following shall be treated as a special design case and the analysis shall be completed prior to application of the repair system.

To account for the limited axial extent [i.e. less than calculated from [Formula \(18\)](#) or [Formula \(19\)](#)] of available substrate ($l_{\text{available}}$), the design repair thickness, t_{design} , determined from either [7.5.4](#), [7.5.5](#), [7.5.6](#), or [7.5.7](#) shall be increased by the repair thickness increase factor, $f_{\text{th,overlay}}$, defined as:

$$f_{\text{th,overlay}} = \left(\frac{l_{\text{over}}}{l_{\text{available}}} \right)^{2/3} \quad (22)$$

where $t_{\text{design}} = f_{\text{th,overlay}} t_{\text{design, original}}$.

The above design procedure represents a conservative approach to determining the axial extent of repair beyond the defect. A more detailed engineering stress analysis of the adhesive layer demonstrating that the axial load can be transmitted between the repair and the substrate may be performed if it is required to optimize the repair design in terms of the repair thickness. This more detailed analysis shall also demonstrate that the average principal stress (averaged over the stressed part of the adhesive layer) is less than three times the average principal stress value from lap shear test data (see [Table 4](#)).

The axial extent of design thickness of repair, l_{over} , shall be at least 25 mm and $f_{\text{th,overlay}}$ shall be no greater than 2,5.

If there is limited axial extent of available substrate, it will not be possible to taper the repair laminate. For this case, the transition between the repair laminate and the restraining substrate, e.g. flange face, shall be as smooth as possible to minimize stress concentrations. However, where possible, the repair laminate should always be tapered, particularly when axial loads are present, in order to minimize edge stresses within the repair laminate.

The total axial length of the repair for reduced axial extent is therefore as given below.

For one-side reduced axial extent, calculate using [Formula \(23\)](#):

$$l = l_{\text{over}} + l_{\text{defect}} + l_{\text{taper}} + l_{\text{available}} \quad (23)$$

For two-sided reduced axial extent, calculate using [Formula \(24\)](#):

$$l = l_{\text{defect}} + l_{\text{available},1} + l_{\text{available},2} \quad (24)$$

where the larger of the two values of $f_{\text{th,overlay}}$ is taken to determine the design thickness of the repair [[Formula \(22\)](#)].

When applying repairs over components, e.g. flanges, clamps, etc., to achieve the appropriate total axial length of repair, the axial profile of the repair shall be as smooth as is practically possible to reduce sharp changes in diameter, thus minimizing local stress concentrations. This may result in a thickening of the repair to ensure a smooth axial profile.

When applying repairs up to raised faces, the transition from the repair to the raised face shall be contoured to avoid sharp changes in directions. If required, a more detailed analysis should be performed to demonstrate the axial length of repair is sufficient to transfer the load between the substrate and the repair.

7.5.9 Optional design considerations

7.5.9.1 Impact

The repair system supplier shall demonstrate that the repair to a through-wall defect (type B defect) is capable of withstanding a low-velocity 5 J impact representative of a dropped tool. The demonstration test shall be carried out in accordance with the procedure described in [Annex F](#). This test shall be used to define the minimum repair thickness when the repair is exposed to the possibility of third-party impacts (see [7.5.14](#)).

7.5.9.2 Cyclic loading

Cyclic loading is not necessarily limited to internal pressure loads. Thermal and other cyclic loads shall also be considered when assessing cyclic severity.

If the predicted number of pressure or other loading cycles is less than 7 000 over the design life, then cyclic loading shall not be considered (in accordance with ISO 14692).

If the predicted number of pressure or other loading cycles exceeds 7 000 over the design life, then cyclic loading shall be considered.

If the predicted number of pressure or other loading cycles exceeds 150×10^6 over the design life, then in [Formulae \(26\)](#) and [Formula \(27\)](#), N shall be set to 150×10^6 .

For [7.5.4](#) and [7.5.5](#), the composite laminate allowable strain in both circumferential and axial directions, ε_c and ε_a , (see [Table 9](#)), shall be de-rated by the factor, f_c , i.e.:

$$\begin{aligned} \varepsilon_c &= f_c \varepsilon_{c,\text{non-cyclic}} \\ \varepsilon_a &= f_c \varepsilon_{a,\text{non-cyclic}} \end{aligned} \quad (25)$$

where

$\varepsilon_{a,\text{non-cyclic}}$ is the allowable strain in the axial direction [as defined in [Formula \(10\)](#)] prior to de-rating for cyclic loading, expressed in millimetres per millimetre;

$\varepsilon_{c,\text{non-cyclic}}$ is the allowable strain in the circumferential direction [as defined in [Formula \(10\)](#)] prior to de-rating for cyclic loading, expressed in millimetres per millimetre.

f_c is given by:

when $R_c > 0,4$:

$$f_c = 1,25 \left(\frac{R_c - 1}{\log(150 \times 10^6) - \log(7\,000)} \right) \log(N) + 1 - \tan \left[1,25 \left(\frac{R_c - 1}{\log(150 \times 10^6) - \log(7\,000)} \right) \right] \log(7\,000) \quad (26)$$

when $R_c \leq 0,4$:

$$f_c = \left(\frac{-0,75}{\log(150 \times 10^6) - \log(7\,000)} \right) \log(N) + 1 + 0,75 \left(\frac{\log(7\,000)}{\log(150 \times 10^6) - \log(7\,000)} \right) \quad (27)$$

where

R_c is the cyclic loading severity, defined as the ratio of minimum pressure to maximum pressure: $R_c = \frac{p_{\min}}{p_{\max}}$;

N is the number of loading cycles.

For 7.5.7, the service factor, f_{leak} , in Formulae (12), (13), (14), (15) or (17) shall be calculated using Formula (28):

$$f_{\text{leak}} = 0,333 f_c \quad (28)$$


Formulae (26) and (27) are intended primarily for cyclic internal pressure loading, but may be applied with caution to axial and thermal loads provided they remain tensile, i.e. the formulae are not applicable for reversible loading.

7.5.9.3 Live repairs

If repairs are applied to substrates under live conditions, then the strength and fracture toughness of the bond at the interface between the repair laminate and substrate shall be assessed for the specific case during operation when the internal pressure, p_{after} , after repair system is applied is less than the internal pressure, p_{live} , within the substrate during application of the repair, i.e. $p_{\text{after}} < p_{\text{live}}$.

To assess the strength of the bond of the repair interface, the tensile stress acting on the bond, q (expressed in megapascals), shall be compared to the minimum bond strength defined in Annex B (lap shear strength).

Figure 3 schematically describes the key variables, where, q is the tensile pressure acting on the interface between the repair laminate and the steel substrate when the pipe is depressurised. This tensile stress is due to the fact that the steel substrate contracts more than the composite laminate.

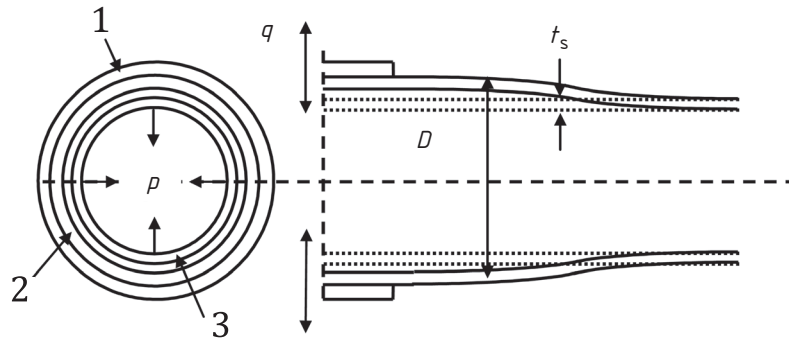

Key

- 1 repair
- 2 pipe before repair (live)
- 3 pipe after repair
- p design internal pressure
- q tensile pressure (stress) on the interface
- D external pipe diameter
- t_s minimum remaining substrate wall thickness

Figure 3 — Schematic diagram of live repair

The tensile stress, q (expressed in megapascals), acting on the interface is given by [Formula \(29\)](#):

$$q = (p_{\text{live}} - p_{\text{after}}) \left(1 - \frac{E_s t_s}{E_s t_s + E_c t_{\text{design}}} \right) - (\alpha_c - \alpha_s) (T_{\text{live}} - T_{\text{after}}) \frac{2E_c t_{\text{design}}}{D} \quad (29)$$

where

- p_{live} is the internal pressure when repair is applied, expressed in megapascals;
- p_{after} is the internal pressure after repair is applied, expressed in megapascals;
- E_c is the circumferential tensile modulus of repair laminate, expressed in megapascals;
- E_s is the tensile modulus of the substrate, expressed in megapascals;
- t_{design} is the thickness of repair laminate, expressed in millimetres;
- α_c is the repair laminate thermal expansion coefficient, circumferential direction, expressed in millimetres per millimetre degree Celsius;
- α_s is the substrate thermal expansion coefficient, expressed in millimetres per millimetre degree Celsius;
- T_{live} is the temperature when repair is applied, expressed in degree Celsius;
- T_{after} is the temperature after repair is applied, expressed in degree Celsius;
- D is the external diameter of substrate, expressed in millimetres.

The value of q shall be less than the short-term lap shear strength divided by a factor of three (see [Annex B](#)). This assessment is approximate but will provide a conservative result.

7.5.9.4 Fire performance

The requirements for fire performance shall be identified by the owner in the repair feasibility assessment. Flame spread and smoke generation shall also be considered in the assessment. Due account shall be taken of the response of the repair system. In many cases, additional fire protection is not necessary, as the substrate may still be able to perform satisfactorily during the short duration of a fire event. However, conduction from the metal substrate can cause the temperature of the repair laminate to exceed its design temperature, limiting the performance of the repair system.

Strategies for achieving fire performance include the following:

- application of additional repair material such that enough basic composite laminate will remain intact for the duration of the fire event;
- application of mineral wool;
- application of intumescent external coatings;
- application of intumescent and other energy-absorbent materials within the repair laminate;
- use of resin formulations with specific fire retardant properties.

Further guidance on the design and testing of composite laminates for fire performance is contained in ISO 14692.

Further guidance on the fire test performance properties of repair laminates, smoke index, flame spread index and fuel contribution index is contained in ASTM E84.

7.5.9.5 Cathodic disbondment

For repairs to substrates that are cathodically protected, it may be required to demonstrate that the repair will not disbond due to the cathodic protection system.

ASTM G8 shall be used to demonstrate that the repair system is not susceptible to disbondment under an imposed electrical current.

7.5.9.6 Electrical conductivity

For repairs to metallic substrates, it is likely that the properties of the substrate will satisfy electrical conductivity requirements.

If the substrate is insulating, e.g. composed of FRP and electrical conductivity (build-up of static charge) requirements are specified, the electrical conductivity properties of the repair system shall be measured to ensure that the original characteristics of the substrate are restored.

Electrical conductivity testing shall be carried out in accordance with ISO 14692.

7.5.9.7 External loads

The minimum repair thickness, t_{\min} (expressed in millimetres), to resist external pressure or vacuum applied to the repair system is given by [Formula \(30\)](#):

$$t_{\min} = \left(\frac{2lD^{3/2}p_e}{3\sqrt{2}E_c} \right)^{0,4} \quad (30)$$

The minimum repair thickness, t_{\min} (expressed in millimetres), to resist soil loads to prevent collapse of a buried repaired substrate is given by [Formula \(31\)](#):

$$t_{\min} = D \left[\frac{3(1-\nu^2)p_{\text{ext,soil}}}{2E_c} \right]^{1/3} \quad (31)$$

$$\text{where } p_{\text{ext,soil}} = \frac{4}{\pi D} \left[D\left(h + \frac{D}{2}\right) - \frac{\pi D^2}{8} + \frac{1}{3}\left(h + \frac{D}{2}\right)^2 \right] \gamma_{\text{soilg}}$$

where

- p_e is the external or vacuum pressure, expressed in megapascals;
- $p_{\text{ext,soil}}$ is the external soil pressure, expressed in megapascals;
- ν is the Poisson's ratio of the repair laminate (see [Annex B](#) for definition);
- D is the external diameter of substrate, expressed in millimetres;
- E_c is the circumferential tensile modulus of repair laminate, expressed in megapascals;
- h is the burial depth (to centreline), expressed in millimetres;
- l is the length of the repair taken as $l_{\text{defect}} + 2l_{\text{over}}$, expressed in millimetres;
- γ_{soilg} is the specific weight of soil, expressed in megapascals per millimetre.

The design repair thickness, t_{design} , shall be the maximum value of the minimum repair thickness determined from [Formula \(30\)](#) or [\(31\)](#) and the design repair thickness derived in [7.5](#).

Further guidance on trench back-fill and other loadings can be obtained from ISO 14692 and AWWA M45.

7.5.10 Dent and/or gouge type defects

All gouges shall be removed by grinding. The remaining dent and, if relevant, the remaining wall thickness after gouge removal shall be assessed by the relevant defect assessment code or standard to determine the MAWP, p_s . The design of the repair shall follow [7.5.4](#).

7.5.11 Fretting type defects

When designing a repair where fretting is an issue, then the fretting resistance of the repair shall be considered including the use of an outer protective layer, such as an elastomeric or rubber pad placed between the repair laminate and the fretting surface.

7.5.12 Delamination or blister type defects

The design of the repair for delamination or blister type defects (within the substrate) shall follow [7.5.5](#), i.e. it shall be assumed that the repair system withstands the applied load with no allowance for the remaining strength of the pipe substrate.

7.5.13 Repair of other components

Qualification of the repair system for other components shall be as defined in [B.7](#).

7.5.13.1 Piping system components

The following piping system components are considered:

- bends;
- tees;
- reducers;
- flanges.

The repair design procedure for each piping system component is a comparative approach based on the equivalent straight pipe component (same diameter and thickness). The repair design process is to calculate the thickness of the repair for an equivalent straight pipe section followed by a further calculation for the repair thickness increase factor, which accounts for the stress intensification due to the geometry of the component.

The first step in the design approach is to calculate the thickness of the repair for the equivalent pipe section of the component as described in [7.5](#), $t_{\text{design, straight pipe}}$ (expressed in millimetres). This repair thickness includes both the repair strength calculation ([7.5.4](#) or [7.5.5](#)), as well as the leak sealing calculation ([7.5.7](#)), if appropriate. Performance data can be used if available following [7.5.6](#). The second step is to calculate the repair thickness increase factor based on the stress intensity factor corresponding to the piping system component, $f_{\text{th, stress}}$.

The design repair thickness, $t_{\text{design, component}}$ (expressed in millimetres), is given by [Formula \(32\)](#):

$$t_{\text{design, component}} = t_{\text{design, straight pipe}} f_{\text{th, stress}} \quad (32)$$

[Table 11](#) presents repair thickness increase factors, $f_{\text{th, stress}}$, for each piping component.

Table 11 — Repair thickness increase factors for piping system components

Piping system component	Repair thickness increase factor $f_{\text{th, stress}}$
Bend	1,2
Tee	2
Flange	1,1
Reducer	1,1

The axial length of the repair shall be calculated from [7.5.8](#).

For tees, the main diameter is defined as that pipe that contains the defect. This pipe diameter shall be used to calculate the repair thickness from the equivalent straight pipe section. The repair thickness increase factor is then applied to this repair thickness.

The axial length of repair shall be based on the (larger) dimension of the piping system component and applies to both the axial length of repair along the main body and branch (where appropriate).

For the repair of tees, the maximum allowable design pressure, p (expressed in megapascals), for the repair laminate design thickness, $t_{\text{design,component}}$ (expressed in millimetres), shall be restricted to:

$$p \leq \frac{2E_c \varepsilon_c t_{\text{design,component}}}{D + D_b} \quad (33)$$

where

ε_c is the circumferential design strain of the composite repair system;

D is the external diameter of main body, expressed in millimetres;

D_b is the external diameter of branch, expressed in millimetres;

E_c is the circumferential tensile modulus of repair laminate, expressed in megapascals.

7.5.13.2 Tank and vessel components

The following tank and vessel components are considered:

a) cylindrical vessels:

- 1) end dome (circular and torisphoidal), main body connection;
- 2) supports/saddles/rigid attachments;
- 3) tees/nozzles.

b) spherical vessels:

- 1) supports/saddles/rigid attachments;
- 2) tees/nozzles.

For tanks and vessels, there are currently few applications, implying less validation of the proposed empirical rules for the design of the repair system.

The repair design procedure for each vessel component is the same as that described in [7.5.13.1](#). [Table 12](#) and [Table 13](#) present repair thickness increase factors for cylindrical and spherical tank and vessel components respectively.

The axial extent of the repair shall be calculated from [7.5.8](#).

Table 12 — Repair thickness increase factors for cylindrical vessel components

Cylindrical vessel component	Repair thickness increase factor $f_{\text{th, stress}}$
End dome, main body connection	1,1
Supports, saddles, rigid attachments	1,5
Tees, nozzles	2

Table 13 — Repair thickness increase factors for spherical vessel components

Spherical vessel component	Repair thickness increase factor $f_{\text{th, stress}}$
Supports, saddles, rigid attachments	1,5
Tees, nozzles	2

The axial extent of repair shall be based on the (larger) dimension of the main body and applies to the axial length of repair along both the main body and branch (where appropriate).

For the repair of tees or nozzles, the maximum allowable design pressure, p (expressed in megapascals), for the repair laminate design thickness, $t_{\text{design,component}}$ (expressed in millimetres), shall be restricted to [Formula \(34\)](#):

$$p \leq \frac{2E_c \varepsilon_c t_{\text{design,component}}}{D + D_b} \quad (34)$$

where

ε_c is the circumferential allowable design strain, expressed in millimetres per millimetre;

D is the external diameter of main body, expressed in millimetres;

D_b is the external diameter of branch, expressed in millimetres;

E_c is the circumferential tensile modulus of repair laminate, expressed in megapascals.

Patch repairs are acceptable provided it is demonstrated that the performance is equivalent to a fully circumferential repair and that the axial extent of the repair is at least that defined in [7.5.13.4](#).

7.5.13.3 Clamps and other repair systems

Clamps are generally applied over defects much smaller than themselves. The clamp protrudes or stands off a set height from the pipework. The size of the effective defect is a function of the geometry of the clamp or repair system. Often, the outer surface of the clamp is not smooth, e.g. bolts, etc., implying it may not be possible to achieve a large enough outer surface area for adequate bonding.

If good bonding between the repair laminate and the full outer surface of the clamp can be demonstrated, 360° around the circumference and along the full length of the clamp, e.g. through coupon pull-off tests or qualification tests on the clamp casing material, then the effective size of the defect shall be a fully circumferential defect at each end of the clamp of axial extent 1,5 times the stand-off height. Either [Formula \(13\)](#) or [Formula \(14\)](#) shall be used to calculate, iteratively, the minimum repair thickness, t_{min} (expressed in millimetres).

If good bonding between the repair laminate and the clamp surface cannot be demonstrated 360° around the circumference and along the full length of the clamp, e.g. for clamps with axially orientated flanges or other tightening mechanisms, then the effective size of the fully circumferential defect shall be the axial extent of the clamp plus an axial distance of three times the stand-off distance. [Formula \(13\)](#) shall be used to calculate the minimum repair thickness, t_{min} (expressed in millimetres). The final repair thickness shall be calculated using [Formula \(32\)](#) where $f_{\text{th,stress}}$ is taken as 1,5.

The same principle as outlined for clamps shall also apply to the repair of non-engineered repair systems.

The size of the defect shall be taken as the total axial length of the existing repair (axial extent of repair plus taper length) and [Formula \(13\)](#) or [Formula \(14\)](#) shall be used to calculate the minimum repair thickness, t_{min} (expressed in millimetres). The final repair thickness shall be calculated using [Formula \(32\)](#) where $f_{\text{th,stress}}$ is taken as 1,1.

The axial extent of the repair to either clamps or non-engineered repairs shall be calculated using [Formula \(18\)](#).

7.5.13.4 Patches

Repair patches are used when it is impractical for the repair to encompass the full circumference of the component. Typically, these components are limited to large diameter (greater than 600 mm) pipework, pipelines or vessels.

The thickness of the repairs shall be calculated according to [7.5](#) with reference to the relevant component type.

The axial extent of the patch repair shall be the same in both the axial and circumferential directions. The axial extent of the repair shall be calculated according to [7.5.8](#).

7.5.14 Design output

The outputs of the design calculations for the repair system are the following:

- thickness of the repair laminate, t_{design} , expressed in millimetres and number of layers, n ;
- total axial repair length, l , expressed in millimetres;
- axial extent of repair, l_{over} , expressed in millimetres;
- cure schedule required, expressed in minutes or hours at temperature in degree Celsius.

The design thickness of the repair shall be expressed as number of layers, n , for installation purposes, in accordance with [Formula \(35\)](#):

$$n = \frac{t_{\text{design}}}{t_{\text{layer}}} \quad (35)$$

where t_{layer} is the thickness of an individual layer of repair laminate, expressed in millimetres.

The minimum design thickness for the repair laminate is given by

- type A repairs. The greater thickness of either two layers or 2 mm whichever is the greater, and
- type B repairs. That qualified by testing as described in [7.5.9.1](#). Where the potential for external third-party accidental impacts is agreed by the owner to be unlikely the minimum thickness requirement may be relaxed to the greater of two layers or 2 mm.

7.6 Re-qualification of the repair system

7.6.1 Overview

If a change or modification to the repair system has occurred, then the testing specified in [7.6.2](#) and [7.6.3](#) shall be completed.

If the modified repair system is found to be of lower performance than the original repair system, then it shall be treated as a new system and validated according to [7.4.5](#).

If the modified repair system is found to be of higher performance than the original repair system, then it may be treated as a new system and validated according to [7.4.5](#), or the qualification data from the original repair system may be used.

7.6.2 For type A defect repairs

Re-qualification tests shall include the testing specified in [B.2](#).

If the repair system has been validated according to [B.6](#), then the repair system shall be subject to the survival testing specified in [E.2.1](#).

7.6.3 For type B defect repairs

Re-qualification tests shall include the testing specified in [B.2](#) and [B.3](#).

Note that only three tests are required and results shall be compared with γ_{LCL} of the original repair system, [D.4](#).

8 Installation

8.1 Storage conditions

Storage of material shall comply with the repair system supplier's instructions. MSDS sheets shall be retained for reference. All materials shall be stored and controlled according to national safety regulations (e.g. OSHA, COSHH or similar regulations).

All materials shall be clearly labelled with relevant health and safety data, batch number, expiry date and any other relevant technical information.

Control of the temperature during storage shall be maintained. (Shelf lives can be reduced significantly if temperatures are allowed to exceed those specified by the repair system supplier.)

Reinforcements shall be stored to ensure that condensation due either to storage of material below the dew point or on movement between areas at different temperatures does not occur.

Shelf lives quoted by the repair system supplier shall be observed.

Disposal of time-expired material shall be carried out in compliance with local regulations and according to repair system supplier's instructions.

8.2 Documentation prior to repair application

8.2.1 Method statement

Each repair shall be covered by a method statement which is often generic in nature that describes the main procedures to be carried out prior to and during repair system application.

Typically, the method statement provided by the repair system supplier includes the following information:

- a) **Health and safety**, comprising
 - 1) list of materials to be handled including copies of MSDS sheets and COSHH statements,
 - 2) details of protective measures to be adopted, and
 - 3) list of hazards associated with equipment to be repaired and equipment in the vicinity of the repair site with protective measures;
- b) **Quality assurance**, comprising
 - 1) generic overall QA plan, and
 - 2) generic details of hold/inspection points in the repair application procedure (see [8.4](#));
- c) **Installation procedure**, including generic overview of installation procedure;
- d) **Environmental**, including information on disposal of unused material.

8.2.2 Work pack

Each repair shall also be covered by a work pack which is specific and relates directly to the procedures to be performed prior to and during repair system application.

Typically, the work pack provided by the repair system installer includes the following information:

- a) **Scope of work**, including specific details of the design conditions and status of the component requiring repair;
- b) **Health and safety**, including MSDS sheets for the materials to be used and related COSHH statements;
- c) **Risk assessment**, including details of tool box talk with site personnel;
- d) **Repair details**, including drawing of planned repair, thickness, and dimensions of repair and cure schedule;
- e) **Installer qualification level**, defining whether a supervisor is required for the specific application;
- f) **Specific installation instructions**, including any amendments to the generic installation instructions provided in the method statement. These instructions shall include
 - 1) acceptable environmental conditions of site at time of repair,
 - 2) material storage,
 - 3) surface preparation,
 - 4) resin system mixing,
 - 5) laminate lay-up for the component geometry,
 - 6) laminate consolidation procedure (fibre wetting),
 - 7) cure schedule as defined in [7.5.3](#), and
 - 8) key hold points.

Further details of these requirements are listed in [Annex J](#). The key hold points to be observed during repair system installation are dependent on the repair class and are summarized in [Table 14](#).

- **Quality assurance**, comprising and specific amendments to the generic QA plan provided in the method statement, e.g. details of any materials tests to be carried out, if specified by the owner (see [Annex B](#)).
- **Installer certification**, comprising a named list of the installers and their individual qualification certifications.

8.3 Installer qualifications

Personnel involved in the installation of a repair system shall be trained and qualified in accordance with [Annex I](#).

8.4 Installation procedure

The repair system supplier shall provide full installation instructions.

Table 14 — Hold points during installation of a repair system

Hold point	Class	Checked by
Method statement	All classes	Installer
Materials preparation		Installer
— reinforcement	All classes	
— resin	All classes	
Environmental conditions		Installer
— relative humidity	All classes	
— dew point	All classes	
— component surface temperature	All classes	
Surface preparation		Installer (Class 1) Supervisor (Classes 2 and 3)
— inspection	All classes	
— surface profile test	Class 3	
— mechanical test (stipple test)	Class 3	
Filler profile	All classes (where appropriate)	Installer
Stage check on reinforcement fibre or cloth orientation	Class 3	Installer
Tests on repair laminate		Installer (Class 1) Supervisor (Classes 2 and 3)
— cure (and post-cure) through hardness test or time-temperature measurements taken from the repair	All classes	
— thickness	All classes	
— repair axial extent and taper length	All classes	
— external inspection (see Table 16)	All classes	
QA records	All classes	Installer (Class 1) Supervisor (Classes 2 and 3)
Pressure test		Inspection authority

8.5 Repair completion documentation

The following documentation shall be provided by the repair system installer to the owner on completion of the repair. All records should be retained by both the owner and repair system installer for the duration of the repair design lifetime.

- a) **Repair details**, comprising
 - 1) repair reference number,
 - 2) location of repair.
- b) **Repair design**, comprising details of laminate lay-up:
 - 1) design data ([Annex A](#)) and calculations;
 - 2) repair sketch;
 - 3) number of layers;
 - 4) repair area covered including axial extent;

- 5) orientation of individual layers of reinforcement (this may be presented as a written description or a drawing incorporating standard details such as overlap and taper dimensions and length information).
- c) **Material records**, comprising
 - 1) repair system supplied,
 - 2) resin type and quantity,
 - 3) reinforcement type and quantity,
 - 4) batch number of materials.
- d) **Repair application**, comprising
 - 1) details of surface preparation procedure, including method of application, equipment used and inspection and testing method,
 - 2) details of actual defect size and location,
 - 3) details of the environmental conditions including dew point temperature, ambient temperature, substrate temperature and relative humidity and any relevant limitations,
 - 4) details of the filler used to achieve a smooth outer profile prior to the application of the laminate,
 - 5) details of time limitations between stages of the repair, e.g. between surface preparation and lamination,
 - 6) details of the mixing of the resin and hardener,
 - 7) details of lay-up procedure including orientation of the repair laminate, including also if the repair laminate was applied in stages,
 - 8) details of curing schedule and comparison with specified cure schedule (if carried out - usually Class 3 repair only).
- e) **Quality control records**, comprising
 - 1) repair reference number,
 - 2) visual inspection report,
 - 3) thickness measurement,
 - 4) repair axial extent measurement,
 - 5) curing details (time, temperature) and if performed post curing details, temperature and time,
 - 6) personnel (installer) applying the repair system,
 - 7) Barcol or Shore hardness measurement (if carried out),
 - 8) DSC measurement (if carried out),
 - 9) bond strength measurement (if carried out),
 - 10) Inspection and NDT results (if carried out).
- f) **Independent inspection**, comprising test report (if carried out).
- g) **Service inspection**, comprising details of service inspection intervals and repair condition monitoring guidance ([Clause 9](#)).

8.6 Live repairs

Repairs to defects that are not through-wall within live substrates may be performed, provided that the associated hazards are fully considered in the repair feasibility assessment ([7.1](#)) for the operation, e.g. for grit blasting and heat blankets. This shall include any hazards to surrounding live equipment in addition to that being repaired.

Repairs to defects that are through-wall within live substrates may be performed provided that all leaks can be stopped by alternative means reliably for the duration of the repair application and cure time, and that the leak sealing methods are fully considered in the derivation of the repair thickness in accordance with [7.5.7](#), [7.5.9.3](#), and [7.5.13.3](#).

Post-curing using elevated temperature heating should not be undertaken on live pipes unless it can be demonstrated the required post cure temperature can be achieved within the repair laminate.

8.7 Repair of clamps, piping components, tanks, or vessels

Guidance for the surface preparation of clamps, piping components, tanks and vessels is the same as for repairs on straight pipe (see [Annex J](#)).

The axial profile of the repair laminate in the transition from the main pipe body to the component causing the protuberance should be at least tapered with taper dimension of 3 (axial direction) to 1 (radial direction). The precise details of the repair, e.g. repair laminate lay-up and orientation relative to clamps, piping components, tanks or vessels, shall be provided by the repair system supplier. The arrangements at the edges of the repair, e.g. tapering and profiling onto raised faces, shall also be provided by the repair system supplier.

8.8 Environmental considerations

Only repair materials that allow for satisfactory disposal according to prevailing environmental regulations shall be used as described in [8.2.1](#).

Information and procedures for disposing of unused chemicals, resins and waste shall be provided by the repair system supplier. Incineration in the open air shall not be performed.

9 Testing and inspection



9.1 General

This subclause provides guidance on the post-installation operational issues of repair systems. The installation of a repair system should not influence or prevent any internal inspections (e.g. from pigging inspection tools) that are performed on the substrate.

The main issues for the non-destructive examination of a repair system are the following:

- inspection of the repair laminate;
- inspection of the bond between the repair laminate and the substrate;
- inspection of the substrate underneath the repair laminate.

The basic structure of a repair system in this context is considered in [Figure 4](#).

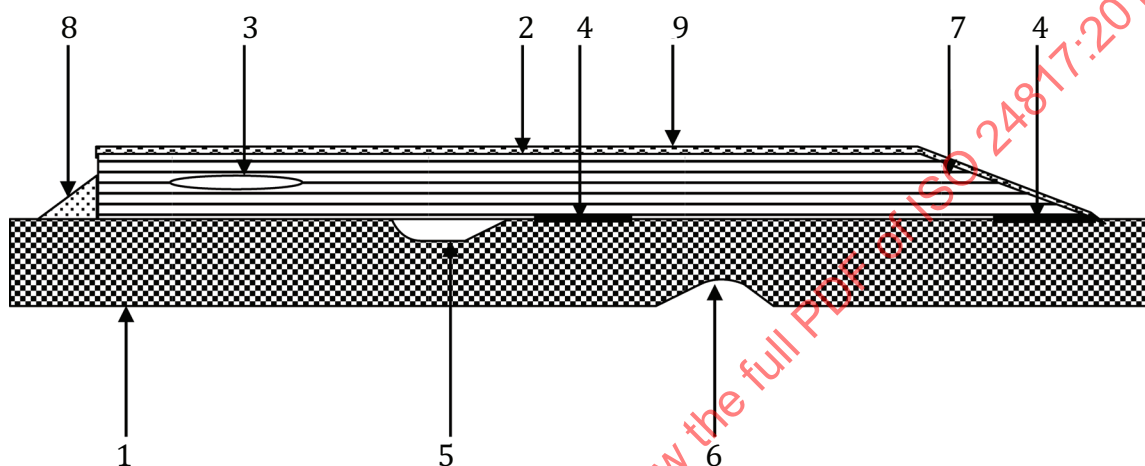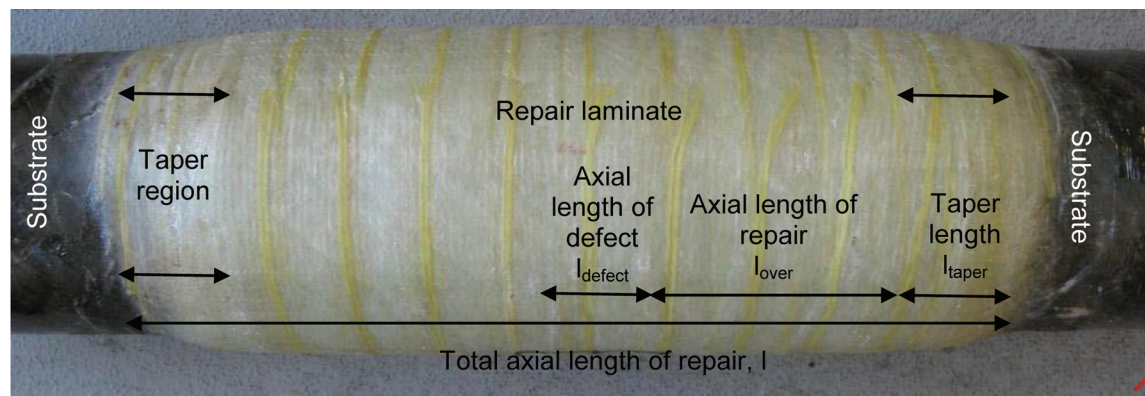

Key

- 1 substrate, pipe wall
- 2 repair laminate
- 3 internal laminate defect
- 4 interface delamination de-bond
- 5 external defect (with filler)
- 6 internal defect
- 7 taper of laminate (extends beyond overlay l_{over})
- 8 adhesive fillet
- 9 resin rich surface layer

Figure 4 — Schematic of a repair system (not to scale) and location of defects

9.2 Allowable defects for the repair system

The defect types and respective allowable limits for the different sections of the repair system are given in [Table 15](#) prior to application of the repair and in [Table 16](#) for after installation of the repair and in service.

The defects that are listed for the repair laminate and resin-rich layer are likely to arise during installation, as opposed to being caused as a result of deterioration in service. As a result, process control and monitoring of the repair material as it is being applied is the primary means of assuring good quality. The information given in [Table 16](#) is typical of that used for composite process equipment, e.g. GRP piping (see ISO 14692).

The defects that are listed for the interface between the repair laminate and the substrate refer primarily to the loss of adhesion. As with the repair laminate, the defects listed for the interface are generated during initial application. In the majority of cases, deterioration during service manifests itself as an interfacial delamination.

Table 15 — Quality assurance checks for the substrate prior to application of the repair

Repair section	Defect	Allowable Limits
Substrate prior to repair application	Check substrate material is that for which the repair has been designed	
	Changes in geometry	Repair area to be free of sharp changes in geometry (all radii > 5 mm) or sharp geometry to be faired-in
	Surface preparation	In accordance with repair system specification Axial length to be in accordance with design
	Surface temperature	In accordance with repair design
	Defect	Dimensions do not exceed those for which the repair has been designed Defect nature to be that for which the repair has been designed
	Location of repair	Axial extent and positioning to be in accordance with design

Table 16 — Inspection requirements for the repair laminate after installation and in service

Repair section	Defect	Allowable Limits
Interface between pipe and repair at the ends of the repair, including adhesive fillets	Delamination (cracks between the pipe and the repair)	None allowed Tap test may help identify presence of delaminations
Surface of repair (Resin-rich layer)	Cracks	None that penetrate into the repair laminate
	Foreign matter and, blisters	Maximum 10 mm in width, 1,5 mm in height
	Pits	Maximum 25 mm in diameter, 1,5 mm in depth No limit for depths shallower than 1 mm
	Wrinkles	No step changes in thickness in height greater than the lower of 1,0 mm or 20 % of the repair laminate design thickness
	Pin holes	None deeper than resin-rich layer
	Resin colour	Uniform
	Dry spots	None
	Finishing materials	None (should be fully removed before inspection is completed)
Repair laminate	Fibre orientation	As specified in design
	Un-impregnated/dry fibre	None
	Exposed cut edges/fibres	None
	Foreign matter	None







Table 16 (continued)

Repair section	Defect	Allowable Limits
	Axial extent and positioning of the repair	As specified in the design
		Does not extend beyond prepared surface
	Impact damage	None
	Delamination within laminate	None allowed Tap test may help identify presence of delaminations

The defects that are listed for the substrate relate to those that have been repaired and to possible continued degradation of the wall thickness after repair due to internal corrosion or erosion. Monitoring of the remaining wall thickness may be required to ensure that the repair system continues to operate within the original design assumptions.

[Table 17](#) presents a pictorial representation of some of the typical defect types that can occur in a repair system after installation and during service. The photographs in [Table 17](#) are intended to aid the interpretation of the defects listed in [Table 16](#) and their respective allowable limits.

Table 17 — Pictorial description of defects after installation and in-service

	
Interfacial delamination	Interfacial delamination
	
Impact damage – glass fibre based repair	Impact damage – carbon fibre based repair
	
Dry fibres	Exposed fibres

9.3 Repair of defects within the repair system

Repairs containing defects that exceed the limits in [Table 15](#) and [Table 16](#) should be removed and another repair system applied. However, on agreement with the owner, local removal of the damaged area and reapplication of the repair system materials to this area are allowable if the repair system supplier can demonstrate that this will restore the full performance of the repair.

Dry areas in the resin-rich surface layer should be repaired by abrading and cleaning the affected area and then wetting out with more resin.

9.4 Inspection methods

The repair system supplier should provide guidance on techniques and methods for inspecting the repair system. Further guidance could be provided by inspection technology companies. Inspection techniques may be applied immediately after the repair system application as a base line measurement or during the repair design lifetime. In most cases, the requirement is not to inspect the composite laminate, but to inspect the defect within the substrate with the overall aim of demonstrating the integrity of the complete system, i.e. substrate and repair.

9.5 Repair system maintenance and remedial options

9.5.1 Overview

The appropriate maintenance and replacement strategy for repair systems is a function of the type of original defect in the substrate. A risk assessment shall be completed to determine the appropriate strategy and shall consider the guidance given in this subclause. [Annex L](#) provides informative guidance on how to manage the overall integrity of repair system applications.

9.5.2 Condition of the repair - visual inspection

Visual inspection of the repair laminate for defects in accordance with [Table 16](#) and [Table 17](#) is recommended as part of the maintenance strategy. If defects are located, then further assessment shall be made in conjunction with the repair system supplier. The frequency of inspection should be determined in accordance with the risk assessment.

A photograph of the repair should be taken and retained for comparison with future inspections.

Table 18 — Pictorial guide to coating requirements at ends of repairs

	
Coating at end of repair present and good condition	Coating at end of repair has not been installed and corrosion has started

Where the pipe is coated, then in addition to the inspection detailed above, the inspector shall confirm that an additional coating covering the ends of the repair is present and in good condition (see [Table 18](#)). If no coating over the ends of the repair is present and the pipe substrate is in good condition, then a coating should be installed. If corrosion is visible at the ends of the repairs, then the fitness for purpose of the repairs shall be considered by a reassessment of the design requirement.

9.5.3 Condition of the pipe substrate

9.5.3.1 External defects

For external defects, it is assumed that further deterioration of the defect is stopped on application of the repair laminate. Therefore, the maintenance strategy should be to ensure that the repair laminate remains intact, i.e. the repair laminate is not damaged or partially delaminated from the substrate.

Inspection of the pipe beneath the repair should be considered for all Class 3 repairs. Radiography and eddy current techniques have been successful in interrogating the pipe beneath the repair; further advice can generally be obtained from the repair system supplier and specialist inspection companies. It is recommended that a baseline inspection is completed after installation of the repair because it is much simpler to identify changes than to interpret the information gained by subsequent inspections.

For Class 3 repairs with design lifetimes greater than two years, consideration should be given to confirming that internal corrosion has not commenced. If internal corrosion is determined as active, then a suitable strategy to mitigate the threat should be determined (e.g. change in process conditions, use of inhibitors or reduced life of repair, etc.).

9.5.3.2 Internal or through-wall defects

For internal corrosion or through-wall defects, further deterioration or growth of the defect may continue despite application of the repair laminate. Therefore, in addition to the requirements set out in [9.5.3.1](#), the maintenance strategy should ensure that the internal defect does not grow to a size greater than assumed in the design or that the repair laminate does not delaminate from the substrate. Therefore, information of the acceptable defect size determined by design shall be retained and be readily available.

The frequency of inspection should be determined in accordance with the risk assessment.

Inspection of the pipe beneath the repair shall be considered for all Class 3 repairs the objective being to demonstrate the defect in the pipe remains within the acceptable limit determined by design. Again, radiography and eddy current techniques have been successful in interrogating the pipe beneath the repair; further advice can generally be obtained from the repair system supplier and specialist inspection companies. It is recommended that a baseline inspection is completed after installation of the repair because it is much simpler to identify changes than to interpret the information gained by subsequent inspection.

9.5.4 Remedial options

If the assessment determines that replacement is required, then remedial options include the following:

- removal of the repair (e.g. through ultra-high-pressure water jetting or grit blasting) and replacement;
- repair of the repair laminate. In this case, the damaged repair laminate should be considered as the defect for design purposes and a new repair designed according to [7.5](#);
- localized repair of the damaged area (see [9.3](#)).
- In the event of interfacial failure of a repair system, the preferred course of action is to remove the repair laminate. The repair of a failed repair by the simple application of additional material, particularly if the leak is caused by a delamination at the repair laminate/substrate interface, is unlikely to be successful and is not recommended.

9.5.5 Extension (revalidation) of repair design lifetime

The decision to extend the repair design lifetime shall be documented along with supporting records which shall be retained for future reference (records shall include the risk assessment, original and any revised design assessments and the original installation documentation for the repair).

9.5.5.1 Class 1 and 2 repairs

For extending the lives of Class 1 and 2 repairs, it may be considered sufficient just to leave repairs in place if failure of the repair leads to a benign leak. If the fluid presents a hazard or the consequence of failure is unacceptable, then the requirements for extending the lives of Class 3 repairs in [9.5.5.2](#) shall be followed.

9.5.5.2 Class 3 repairs

It is possible to revalidate or extend the lifetime of Class 3 repairs. To revalidate the lifetime of a repair, the design and installation details shall be available (these shall include records of the surface preparation of the substrate and the design and cure of the repair met the original specifications) and the installation records sufficient to demonstrate the repair was installed in full compliance with the repair supplier's procedures. It is recommended that repair design lifetimes are only revalidated up to a maximum of 20 years (from the time the repair was installed). Revalidation of the repair design lifetime is performed by redesigning the repair based on the required lifetime and the most up to date inspection data on the defect of concern. This redesign may result in a thicker repair than currently installed which implies that extra layers of repair material shall be added to the existing repair.

For revalidation of lifetimes greater than 20 years, only a moderate lifetime extension is recommended, i.e. increments of no more than five years. It is further recommended that the repair and the substrate underlying the repair are fully inspected before considering revalidation.

Revalidation of the repair design lifetime is performed by redesigning the repair based on the required lifetime and the most up to date inspection data on the defect of concern (see [9.5.3](#)). This redesign may result in a thicker repair than currently installed which implies that extra layers of repair material shall be added to the existing repair.

9.5.6 Future modifications

Existing repair systems may be modified, but only after a design reassessment performed by the repair system supplier. Modifications considered include extension of length of repair or thickness as a result of increased corrosion activity, newly discovered defects or a change in operating parameters. The principles set out in [9.5.5](#) shall be followed.

10 System testing

System pressure testing should be specified by the owner if required or as recommended by the relevant design standard for the substrate.

All repairs shall be cured in accordance with the repair system supplier instructions before system testing.

The repaired system shall be flushed with an appropriate medium prior to testing.

The recommended procedure for hydro-testing is as follows. The hydro-test should be performed at 1,1 times the design pressure for a period of at least 60 min, during which any changes in pressure and temperature shall be recorded. Any signs of leakage from the repair laminate shall be cause for rejection of the repair system.

In some circumstances, the owner may specify a hydro-test to 1,5 times the design pressure instead of the requirements of the previous paragraph. All supports and anchors shall be in place prior to pressure testing. Temporary supports or restraints should be added if necessary.

If the test pressure exceeds the pressure for which the repair system has been designed, then this higher pressure shall be considered as a separate design case. For the purposes of the design calculation, the hydro-test condition shall be treated as an occasional load.

Further guidance on system testing can be found in ASME PCC-2 Article 5.1 or other relevant documents.

11 Decommissioning

Reference should be made to the risk assessment prior to decommissioning of a repair system. If necessary, a separate risk assessment should be carried out.

The removal of repair material may be achieved by mechanical means (e.g. grit blasting and high-pressure water jetting). Procedures should be put in place to contain any dust that may be generated. Care should be taken to avoid damage to adjacent equipment that is to remain in service.

STANDARDSISO.COM : Click to view the full PDF of ISO 24817:2017

Annex A (normative)

Design data sheet

This annex provides an example of a design data sheet. This data sheet shall form the basis of the scope of work provided by the owner to the repair system supplier and shall be used in the preparation of the design of the repair. One sheet shall be completed for each repair required.

Customer details			
Contact			
Company			
Address			
Postcode		Country	
Telephone			
Fax			
E-mail			
Job reference			

Pipe details			
Installation			
Location			
Quantity (number of)			
Pipe identification			
Pipe reference			
Pipe specification			
Material/Grade			
External diameter (mm)			
Original wall thickness (mm)			
Pipe contents			
Design temperature (°C)	Minimum		Maximum
Operating temperature (°C)	Minimum		Maximum
Pipe coating (existing)			
Existing repair on pipe for leak sealing			

Repair class and lifetime	
Repair class	
Repair design lifetime (years)	
Other data	

Loading	Operating	Design	Test	Comments
Pressure rating (MPa)				
Axial Load (kN)				
Bending moment (Nm)				
Shear load (kN)				
Torsion (Nm)				
Other loads (N)				
NOTE 1 Any original design calculations, piping isometrics should be appended to this datasheet.				
NOTE 2 Loads should be defined as either sustained or occasional in the comments column.				

[illegible]

Repair specification				
Type of defect				
Nature of defect				
Current size	Area (mm ²)		Depth (mm)	
Projected size	Area (mm ²)		Depth (mm)	
Cause	Corrosion		Erosion	
Effect	External		Internal	
	Perforated			
MAWP (MPa)				

Anticipated conditions during implementation of repair				
Pipe temperature (°C)	Minimum		Maximum	
Ambient temperature (°C)	Minimum		Maximum	
Pipe pressure (MPa)				
Pipe contents				
Humidity (%)				
External environment				
Constraints				

Facilities to be provided by client/installation (surface prep., etc.)

Other information
NOTE This should include any remarks on previous repairs, fire protection requirements, etc.

Prepared by:

Date:

STANDARDSISO.COM : Click to view the full PDF of ISO 24817:2017

Annex B (normative)

Qualification data

B.1 General


This annex describes the qualification data that the repair system supplier shall provide.

It is a requirement that all qualification tests be carried out using the same substrate material, surface preparation procedure, repair laminate, filler material, adhesive and application method (see [Clause 5](#)).

B.2 Data for repair laminates

For all repair classes, the following data are required:

- ply or layer thickness of the repair laminate;
- tensile modulus strain to failure and strength in the circumferential direction, determined by test according to [Table 4](#);
- tensile modulus, strain to failure and strength in the axial direction determined by test according to [Table 4](#);
- Poisson's ratio in the circumferential direction (i.e. load direction circumferential, contraction axial), determined by test according to [Table 4](#);
- shear modulus, determined by test according to [Table 4](#). The test specimen geometry is shown in [Table 4](#) and [Figure B.1](#). This figure presents the orientation of the test sample as defined in ASTM D5379. Alternatively, the shear modulus of the resin may be used;

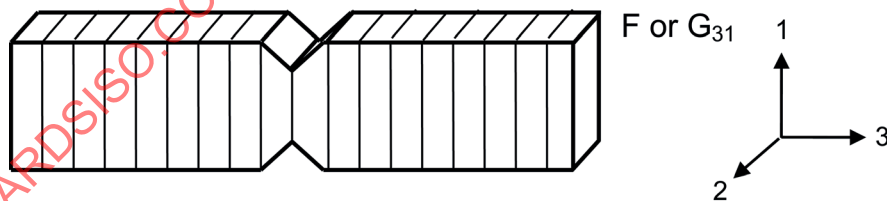

Key

- 1 direction parallel to laminate lay-up (see ASTM D5379, G_{31} for details)

Figure B.1 — Test specimen geometry from ASTM D5379

- Barcol or Shore hardness determined by test according to [Table 4](#);
- glass transition temperatures (T_g) or heat distortion temperatures (HDT) for the resin system, determined by test according to [Table 4](#) for a range of relevant cure times and temperatures. The T_g of a system is not a unique value but will vary with cure temperature and time held at temperature. Where materials are intended for service at above ambient temperature (i.e. $>40\text{ }^{\circ}\text{C}$), then values of T_g shall be measured for a range of cure temperatures at, for example, $10\text{ }^{\circ}\text{C}$ or $20\text{ }^{\circ}\text{C}$ intervals and the relevant value shall be used in the repair design in [7.5.3](#). The installed repair will then be subject to the same cure schedule to ensure the required T_g has been achieved. Many polymer systems exotherm as they cure and this can generate a temperature increase and a high value of T_g . The

peak temperature achieved during curing shall be measured where the stated T_g is more than 30 °C above the cure temperature and this peak shall be replicated on site;

- thermal expansion coefficient in the axial and circumferential directions, determined by test according to [Table 4](#).

B.3 Data for interface adhesion strength

The objectives of the following tests are not to produce data for use in design. The intent is to demonstrate that an adhesive bond can be achieved of adequate strength and durability for the repair laminate. Note that short-term strength measurements are not necessarily a good indicator of long-term performance.

For all repair classes, data on the short-term lap shear strength determined by test according to [Table 4](#) are required. This short-term test shall be used to determine the average shear strength (minimum value 5 MPa) or the locus of failure (composite laminate remaining on a minimum of 30 % of the bonded area). The substrates used in this test should be identical and be of the same material and lay-up as the repair laminate. Alternatively, it shall be demonstrated that the adhesive bond is stronger than the shear strength of the repair laminate by assessing the surface of the substrate material used in a lap shear specimen after testing.

For Class 3 repairs, if evidence of long-term durability of the adhesive bond between the repair laminate and the substrate is required and performance-based testing has not been carried out to provide data for design (see [7.5.6](#)), the long-term lap shear strength shall be determined by test according to [Table 4](#). This test shall be carried out following immersion in water (or other relevant medium) at the design temperature for 1 000 h. The average shear strength determined from this test shall be at least 30 % of the value from the short-term lap shear test determined above.

B.4 Requirements for repairs to substrates with non through-wall defects (Type A design case)

The objective of the short-term pipe spool survival test, in accordance with [Annex C](#), is to define the maximum percentage wall loss that shall be repaired.

B.5 Requirements for repairs to substrates with through-wall defects (Type B design case)

For all repair classes, the following data are required:

- fracture toughness parameter γ_{LCL} , determined by test in accordance with [Annex D](#);
- impact performance, determined by test in accordance with [Annex F](#) which determines the minimum acceptable thickness of repair;
- degradation factor (optional) [Annex G](#).

B.6 Performance testing

The supplier may carry out performance testing to determine design allowables in accordance with [Annex E](#). The long-term strain to failure design allowables are determined by either of the following:

- 1 000-h survival;
- regression testing;
- representative repair laminate coupon regression testing.

B.7 Other components

A single test for each representative pipework components (only bends and tees shall be considered) identical to one of those described in [Annex D](#) (same diameter, wall thickness and one selected defect size) shall be performed on components other than straight pipe sections to demonstrate the repair system performance.

A 90° bend shall be selected as the representative component for pipe bends. The defect location shall be as indicated in [Figure B.2](#).

An equal tee shall be selected as the representative component for pipe tees. The defect location shall be as indicated in [Figure B.2](#).

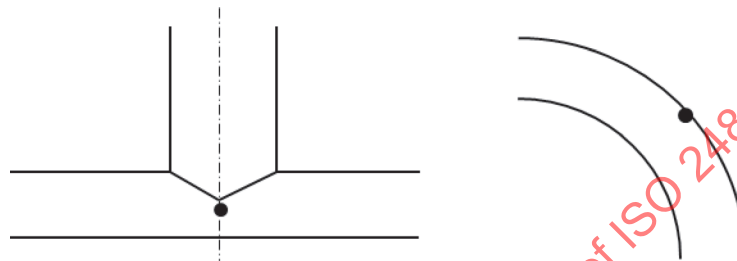


Figure B.2 — Defect location within component

The repair system shall be considered qualified if the failure pressure of the test is greater than or equal to the failure pressure of the equivalent straight pipe section for the appropriately design repair system.

B.8 Summary qualification test reports

The following table shall be presented by a repair supplier to demonstrate compliance with this document.

Repair system name		
Qualification test temperature (°C)		
Repair curing conditions (temperature and time)	Cure temperature (°C)	Cure time (h)
B.2 – Repair laminate data		
Ply or layer thickness (mm)		
Circumferential direction – tensile modulus (GPa)		
Circumferential direction – strain to failure (mm/mm)		
Circumferential direction – tensile strength (MPa)		
Axial direction – tensile modulus (GPa)		
Axial direction – strain to failure (mm/mm)		
Axial direction – tensile strength (MPa)		
Poisson's ratio in the circumferential direction		

Shear modulus (GPa) (refer to Figure B.1)			
Barcol or Shore hardness (of cured laminate)			
Glass transition or heat distortion temperature (°C)	Cure temperature (°C)	Cure time (h)	T_g (°C)
Peak exotherm temperature measured for T_g sample (°C)			
Circumferential direction – thermal expansion coefficient (mm/mm/°C)			
Axial direction – thermal expansion coefficient (mm/mm/°C)			
B.3 – Repair/laminate/substrate interface/surface preparation technique			
Short-term lap shear strength (MPa)			
Long term lap shear strength (MPa)			
B.4 – Short-term pipe spool survival test			
Report on short-term pipe spool survival test as described in C.3			
B.5 is only required to be completed for qualification of Type B repairs			
B.5 Requirements for repairs to substrates with through wall defects			
Report on energy release rate calculation, γ_{LCL} as described in D.5 (including surface preparation method)			
Report on impact performance as described in E.3 (quoting repair thickness and number of layers)			
Optional repair on measurement of degradation factor described in G.4			
B.6 Performance testing - optional			
Report on performance testing as described in E.3			
B.7 Other components			
Tee			
Bend			

Annex C (normative)

Short-term pipe spool survival test

C.1 General

This annex describes the test method for qualification of repairs to non through-wall defects (Type A defect). The purpose of the test is to determine the maximum percentage wall loss that can be repaired.

C.2 Method

The following test shall be completed using a metallic pipe of at least 100 mm diameter and minimum length of six times the diameter in addition to the length of the repair.

A defect shall be machined into the pipe. The defect shall have an axial length, l , of at least one half of the pipe diameter and a circumferential width, w , of at least one-quarter of the pipe diameter. The depth of the defect shall be 80 % of the original wall thickness. A radius may be machined outside the edge of the defect, but the dimensions of machined area shall not exceed $2l$ nor $2w$, as shown in [Figure C.1](#). To avoid stress concentrations, the interior and exterior corners should be machined with a radius. The edge of the repair shall be at least three times the pipe diameter away from the ends of the pipe spool.

The test pressure of the spool, p_f (expressed in megapascals), shall be calculated using [Formula \(C.1\)](#):

$$p_f = \frac{2ts_a}{D} \quad (C.1)$$

where

t is the wall thickness of the undamaged spool, expressed in millimetres;

D is the external pipe spool diameter, expressed in millimetres;

s_a is the measured yield stress or mill certification, expressed in megapascals.

A repair laminate shall be applied to restore the pipe spool to pressure, p_f . The minimum thickness of the repair shall be calculated using [Formula \(C.2\)](#):

$$t_{\text{repair}} = \frac{1}{E_c \varepsilon_{\text{short}}} \left(\frac{p_f D}{2} - s_a t_s \right) \quad (C.2)$$

where

t_s is the remaining wall thickness of the pipe spool at the defect, expressed in millimetres;

E_c is the tensile modulus in the circumferential direction of the composite laminate expressed in megapascals;

$\varepsilon_{\text{short}}$ is the short-term failure strain limit of the composite laminate, defined as 0,008.


The actual repair thickness shall be determined by dividing this calculated thickness by the individual layer or wrap thickness. The required number of wraps of the repair shall be this number rounded up to the next integer. The actual repair thickness shall be the number of wraps times the individual wrap thickness.

The repaired spool shall be pressurized to p_f . Pressure testing shall be in accordance with ASTM D1599.

Successful demonstration requires the repaired pipe spool to survive the pressure loading to p_f . If successful, then the repair system shall be considered qualified for repair of defects up to the selected depth of defect used in the test.

C.3 Report

A report shall be prepared giving the test conditions, details of the repair system and the individual test results and the maximum wall loss that can be repaired.

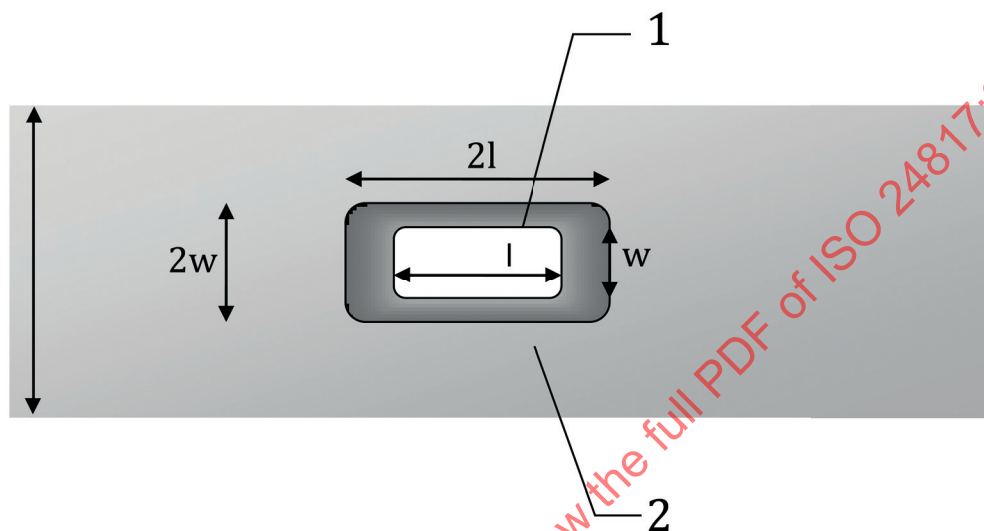

Key

- 1 defect
- 2 machined area (including taper)
- $l > D/2$ and $w > D/4$

Figure C.1 — Defect dimensions

Annex D (normative)

Measurement of γ_{LCL} for through-wall defect calculation

D.1 General

This annex describes the test method for measurement of the toughness parameter (energy release rate) for the repair laminate/substrate interface, γ_{LCL} , to be used in [Formulae \(11\) to \(14\)](#).

D.2 Method

Sections of metallic pipe of minimum diameter 100 mm and minimum thickness 3 mm shall be used. To represent typical defects, circular holes shall be drilled through the wall thickness and the repair laminate applied following the qualification application procedure. The repair system shall be applied with the defects in the 6 o'clock orientation.

The metallic pipe section used for the preparation of the test specimen should be appropriate for the anticipated failure pressure of the repair. Yielding of the pipe prior to failure should not occur.

Internal pressure shall be applied, and the value at which the repair begins to leak shall be recorded.

The test shall be carried out at the qualification test temperature.

The test pressure shall be increased in accordance with ASTM D1599.

A minimum number of nine tests shall be carried out, covering a minimum of three hole sizes, typically of diameters 10 mm, 15 mm and 25 mm. For the larger diameters, the defect may be simulated by using a smaller hole and a circular polymeric release film of the appropriate diameter placed over the hole prior to application of the repair laminate. The holes shall not be filled or sealed by any means (mechanical or chemical) prior to application of the repair.

Failures should take the form of delamination of the repair laminate from the substrate, followed by leaking from the edge of the repair laminate. At small hole sizes, failure can occur through weeping of the test fluid through the thickness of the laminate or through yielding of the substrate. In this event, these tests should be disregarded and a new test carried out using a larger hole size. All failure points should relate to the delamination failure mechanism.

D.3 Calculation of γ_{LCL}

The value of γ_{LCL} , expressed in joules per square metre, shall be calculated by fitting [Formula \(11\)](#) to the data.

The following procedure shall be followed using [Formulae \(D.2\) through \(D.6\)](#) where:

n is the number of observed data points $[A(d_i), p_i]$;

p_i is the pressure, expressed in megapascals, at failure of observation i , where $i = 1, n$;

$A(d_i)$ is the function of defect size and repair laminate properties of observation i , where $i = 1, n$;

$A(d_i)$ is defined as shown in [Formula \(D.1\)](#):

$$p_i = A(d_i)\sqrt{\gamma_i} \quad (D.1)$$

where

$$A(d_i) = \sqrt{\left\{ \frac{0,001}{\frac{(1-\nu^2)}{E_{ac}} \left\{ \frac{3}{512t_i^3} d_i^4 + \frac{1}{\pi} d_i \right\} + \frac{3}{64Gt_i} d_i^2} \right\}} \quad (D.2)$$

and where

E_{ac} is the combined tensile modulus of the repair laminate $\sqrt{E_a E_c}$, expressed in megapascals;

G is the shear modulus of the repair laminate, expressed in megapascals;

ν is the Poisson's ratio of the repair laminate (see [Annex B](#) for definition);

d_i is the diameter of defect, expressed in millimetres;

t_i is the thickness of the repair laminate, expressed in millimetres.

The mean energy release rate, γ_{mean} , is calculated using [Formula \(D.3\)](#):

$$\gamma_{\text{mean}} = \left(\frac{\sum_{i=1}^n A(d_i) p_i}{\sum_{i=1}^n A(d_i)^2} \right)^2 \quad (D.3)$$

The lower confidence limit of the energy release rate, γ_{LCL} , is calculated using [Formula \(D.4\)](#):

$$\gamma_{\text{LCL}} = \left[\frac{\sum_{i=1}^n A(d_i) p_i}{\sum_{i=1}^n A(d_i)^2} - t_v \sigma \sqrt{\frac{1}{\sum_{i=1}^n A(d_i)^2}} \right]^2 \quad (D.4)$$

where σ is the variance of measurement of pressure and is given by [Formula \(D.5\)](#):

$$\sigma = \sqrt{\frac{\sum_{i=1}^n (p_i - A(d_i)\sqrt{\gamma_{\text{mean}}})^2}{(n-2)}} \quad (D.5)$$

and where t_v is the Student's t value and is based on a two-sided 0,025 level of significance, i.e. 95 % lower confidence limit. Values of t_v are given as a function of number of variables, n , in [Table D.1](#).

Table D.1 — Student's t value for double-sided 0,025 level of significance

Number of variables n	Degrees of freedom $n-2$	Student's $t(0,025)$
7	5	2,841
8	6	2,752
9	7	2,685
10	8	2,634
11	9	2,593
12	10	2,560
13	11	2,533
14	12	2,510
15	13	2,490
16	14	2,473
17	15	2,458
18	16	2,445

The value of γ_{LCL} calculated from [Formula \(D.4\)](#) shall be used in [Formulae \(12\)](#) to [\(15\)](#).

D.4 Qualification of other substrates

If the repair system has been fully qualified for one substrate, then a simplified qualification procedure is available for other substrates. In this procedure, only three tests are required to be completed. The three tests should be identical to three of the nine tests in terms of repair thickness and defect size used in the full qualification test programme.

The value of γ for this substrate, substrate 2, $\gamma_{LCL, \text{substrate2}}$, is given by [Formula \(D.6\)](#):

$$\gamma_{LCL, \text{substrate2}} = \gamma_{LCL, \text{substrate1}} \frac{\gamma_{\text{mean, substrate2}}}{\gamma_{\text{mean, substrate1}}} \quad (\text{D.6})$$

In [Formula \(D.6\)](#), “mean” implies the average of the three tests.

D.5 Test report

A report shall be prepared giving the test conditions (including test temperature) and details of the repair method, including the materials of construction and surface preparation technique, the individual data points and the derived value of γ_{LCL} .

Annex E (normative)

Measurement of performance test data

E.1 General

If suppliers carry out performance-based testing, then this annex shall be followed. Suppliers do not have to carry out performance testing to qualify their system; it is an option for them to choose.

This annex describes the test methods for measurement of design allowables to be used in 7.5.6. The test methods options are the following:

- a) survival testing in which the repair system is subjected to a period of sustained load for 1 000 h;
- b) regression testing based on a series of tests on the repair system over different time periods and extrapolation to design life;
- c) regression testing of representative coupons followed by confirmation of long-term coupon test results with survival testing.

All tests shall be carried out at the qualification test temperature.

E.2 Methods

E.2.1 Survival testing

Sections of pipe of minimum diameter 100 mm and minimum thickness 3 mm shall be used and the repair system applied.

A value of internal pressure, p_{test} (expressed in megapascals), shall be applied (as defined by the repair system supplier) and sustained for 1 000 h. If any deterioration of the repair laminate in the form of cracking or delamination occurs, then the repair system shall have failed the test. Three identical tests shall be performed and repair system qualification is only achieved if the repair laminate survives all three tests.

If yielding of the substrate underneath the repair has not occurred, then the 95 % lower confidence long-term strain, ϵ_{lt} (expressed in mm/mm), is calculated using [Formula \(E.1\)](#):

$$\epsilon_{\text{lt}} = \frac{p_{\text{test}} D}{2(E_c t_{\text{min}} + E_s t_s)} \quad (\text{E.1})$$

Otherwise, the 95 % lower confidence long-term strain, ϵ_{lt} (expressed in mm/mm), is calculated using [Formula \(E.2\)](#):

$$\epsilon_{\text{lt}} = \frac{1}{t_{\text{min}} E_c} \left(\frac{p_{\text{test}} D}{2} - s_a t_s \right) \quad (\text{E.2})$$

where

- E_c is the circumferential modulus of the repair laminate, expressed in megapascals;
- E_s is the modulus of the substrate, expressed in megapascals;
- D is the external diameter of test spool, expressed in millimetres;
- s_a is the measured yield stress of the surface or the mill certification yield stress;
- t_{\min} is the thickness of repair laminate, expressed in millimetres;
- t_s is the thickness of substrate test spool, expressed in millimetres.

Further guidance on survival pressure testing procedures may be obtained from ASTM D1598.

E.2.2 Regression testing

Sections of pipe of minimum diameter 100 mm and minimum thickness 3 mm shall be used and the repair system applied.

A series of test specimens shall be subject to sustained pressures of different values. The time at which the repair laminate shows signs of deterioration defined as cracking or delamination shall be recorded. The results shall be plotted (log/log) and the required long-term pressure shall be determined by a regression analysis using the 95 % lower confidence limit and extrapolation to design life.

If yielding of the substrate underneath the repair has not occurred, then the conversion from test pressure, p_{test} (expressed in megapascals) to strain, ϵ_{lt} (expressed in mm/mm), within the repair laminate for each data point shall be carried out using [Formula \(E.3\)](#):

$$\epsilon_{\text{lt}} = \frac{p_{\text{test}} D}{2(E_c t_{\min} + E_s t_s)} \quad (\text{E.3})$$

Otherwise, the 95 % lower confidence long-term strain, ϵ_{lt} (expressed in mm/mm), is calculated using [Formula \(E.4\)](#):

$$\epsilon_{\text{lt}} = \frac{1}{t_{\min} E_c} \left(\frac{p_{\text{test}} D}{2} - s_a t_s \right) \quad (\text{E.4})$$

where

- E_c is the circumferential modulus of the repair laminate, expressed in megapascals;
- E_s is the modulus of the substrate, expressed in megapascals;
- D is the external diameter of test spool, expressed in millimetres;
- s_a is the measured yield stress of the surface or the mill certification yield stress;
- t_{\min} is the thickness of repair laminate, expressed in millimetres;
- t_s is the thickness of substrate test spool, expressed in millimetres.

At least 18 results are required in order to perform the regression analysis. ASTM D2992 provides further guidance on the long-term testing of composite materials and ISO 14692 provides guidance on the analysis of the data to calculate ϵ_{lt} .

E.2.3 Representative coupon testing

Representative coupons of the repair laminate shall be made up and tested in a manner comparable to the actual repair system laminate where representative means having identical laminate constituents, volume fraction and fibre orientation. Comparable loading means coupons shall be loaded identically to the in-service repair laminate (e.g. uni-axial tension or bi-axial tension).

At least 18 coupons shall be tested under constant load to failure (data points in terms of number and length of time of testing in accordance with ASTM D2992, with the statistical analysis of data in accordance with ISO 14692).

The output of these coupon tests is the regression gradient, G , in terms of either the logarithm of the stress or the logarithm of strain plotted against the logarithm of time.

To determine the long-term failure stress or strain of the repair system, five medium-term tests (in accordance with ASTM D1598) shall be performed on sections of pipe of minimum diameter 100 mm and minimum thickness 3 mm. In these tests, the pressure is fixed and the time to failure is recorded. It is recommended to select a test pressure so that failure occurs after about 1 000 h.

The lower confidence limit (in terms of time) for these five tests is calculated according to the mean failure time minus 2 standard deviations. The long-term design strength (or strain) of the repair system is the extrapolation of the lower confidence limit to the repair design lifetime using the measured regression gradient from the coupon tests.

Further guidance on survival pressure testing procedures may be obtained from ASTM D1598.

Further guidance on long-term testing and data interpretation may be obtained from ISO 14692.

E.3 Test report

A report shall be prepared giving the test conditions (including test temperature) and details of the repair method, including the materials of construction and surface preparation technique, the individual data points and the derived performance design data.

Annex F (normative)

Measurement of impact performance

F.1 General

This annex describes the test method for measurement of impact performance. The repair system supplier shall demonstrate that the repair is capable of withstanding the impact from a low velocity 5 J impact representative of a dropped tool. This test is used to determine the minimum thickness of the repair in situations where third-party impacts are considered likely to occur.

F.2 Method

A test specimen identical to one of the nine from [Annex D](#) shall be used.

The repair shall be subject to a 0,5 kg weight with a 12,5 mm hemispherical indenter dropped from a height of 1 m. The pipe shall be supported so that the hole is in the 12 o'clock orientation and the weight shall strike the repair at the position above the hole in the test pipe. The test pipe shall be empty for the duration of the impact test.

The impacted specimen shall then be subject to a pressure test as described in [Annex D](#). The γ value of the test shall be calculated according to [Annex D](#). The calculated γ value shall be no less than γ_{LCL} .

F.3 Test report

A report shall be prepared giving the test conditions (including test temperature), details of the repair system, the individual data points and the derived performance.

Annex G (normative)

Measurement of the degradation factor

G.1 General

This annex describes the test method for measurement of the degradation factor for the repair of through-wall defects (defect Type B) using a low-speed loading rate test. In 7.5.7, a service factor for down-rating the predicted failure pressure is set at 0,333 for a 20-year design life. This factor is based on the product of two effects, the degradation from short-term to long-term failure of the repair laminate plus a safety factor, taken from ISO 14692, of 0,67. In 7.5.7, the default value for the degradation factor is set at 0,5.

G.2 Method

Sections of metallic pipe of minimum diameter 100 mm and minimum thickness 3 mm shall be used. Circular holes shall be drilled through the wall thickness and the repair system applied. All samples shall be laminated with the holes in the 6 o'clock orientation (to minimize the ingress of resin into the defect). A minimum defect size of 25 mm is recommended.

The steel pipe section used for the preparation for the test specimen should be appropriate for the anticipated failure pressure of the repair. Yielding of the metallic pipe prior to failure should not occur.

The thickness of all repairs shall be identical to that used in Annex D.

Internal pressure shall be applied and the pressure value at which the repair begins to leak shall be recorded.

The test shall be carried out at the qualification test temperature.

The test pressure shall be increased daily until the specimen fails. The loading rate shall be such that failure occurs after approximately 1 000 h.

The loading rate for the low-speed loading rate test shall be defined using Formula (G.1):

$$p(t) = p_0 + p_1 t \quad (\text{G.1})$$

where

p_0 is the initial pressure, expressed in megapascals;

p_1 is the fixed linear increase in pressure, expressed in megapascals per hour;

t is the time, expressed in hours.

It is recommended to set the initial pressure, p_0 (expressed in megapascals), to $p_0 = 0,1 p_{\text{sthp}}$ and the linear increase in pressure, p_1 (expressed in megapascals per hour), to $p_1 = 0,9 \times 10^{-3} p_{\text{sthp}}$.

Five tests shall be carried out in total.

Failures should take the form of delamination of the repair laminate from the substrate, followed by leaking from the edge of the repair laminate.

G.3 Calculation of the degradation factor

The short-term failure pressure, p_{sthp} (expressed in megapascals) shall be calculated using [Formula \(G.2\)](#):

$$P_{sthp} = \sqrt{\left\{ \frac{0,001\gamma_{mean}}{\frac{(1-\nu^2)}{E_{ac}} \left\{ \frac{3}{512t^3}d^4 + \frac{1}{\pi}d \right\} + \frac{3}{64Gt}d^2} \right\}} \quad (G.2)$$

where

E_{ac} is the combined tensile modulus $\sqrt{E_a E_c}$, expressed in megapascals;

G is the shear modulus of the repair laminate, expressed in megapascals;

ν is the Poisson's ratio of the repair laminate (see [Annex B](#) for definition);

d is the diameter of defect, expressed in millimetres;

t is the thickness of repair laminate, expressed in millimetres;

γ_{mean} is the mean energy release rate [[Formula \(D.3\)](#)], expressed in joules per square metre.

The average failure pressure of at least five medium-term tests shall be calculated and defined as p_{mthp} .

The regression gradient, B , shall be calculated according to [Formula \(G.3\)](#):

$$B = \frac{1}{\left(\frac{\log\left(\frac{p_{sthp}}{p_1}\right)}{\log\left(\frac{p_{sthp}}{p_{mthp}}\right)} - 1 \right)} \quad (G.3)$$

The degradation factor, f_d , shall be calculated using [Formula \(G.4\)](#), where it is assumed that the design life of the repair is 20 years:

$$f_d = 10^{-5,24B} \quad (G.4)$$

G.4 Test report

A report shall be prepared giving the test conditions (including test temperature), details of the repair system, the individual data points and the derived value of the degradation factor.